AD NUMBER

AD868279

NEW LIMITATION CHANGE

TO

Approved for public release, distribution
unlimited

FROM

Distribution authorized to U.S. Gov't.
agencies and their contractors; Critical
Technology; JAN 1970. Other requests shall
be referred to Air Force Rocket Propulsion
Laboratory, Attn: RPPR/STINFO, Edwards
AFB, CA 93523.

AUTHORITY

AFRPL ltr, 29 Sep 1971

AD 868279

COLD WELDING RESEARCH FINAL REPORT

BY

D. B. SHELDON

PHILCO-FORD CORPORATION
SPACE AND RE-ENTRY SYSTEMS DIVISION

JANUARY 1970

THIS DOCUMENT IS SUBJECT TO SPECIAL EXPORT CONTROLS, AND EACH TRANS-
MITTAL TO FOREIGN GOVERNMENTS OR FOREIGN NATIONALS MAY BE MADE ONLY
WITH PRIOR APPROVAL OF AFRPL (RPPR/STINFO), EDWARDS, CALIFORNIA 93523.

PREPARED FOR:

AIR FORCE ROCKET PROPULSION LABORATORY
AIR FORCE SYSTEMS COMMAND
EDWARDS AIR FORCE BASE, CALIFORNIA

CONTRACT F04611-68-C-0077

DDC

APR 31 1970

C

58

NOTICES

This document is subject to special export controls and each transmittal
to foreign governments or foreign nationals may be made only with prior
approval of AFRPL (RPPR-STINFO), Edwards AFB, California 93523.

When U.S. Government drawings. specifications, or other data are used for
any purpose other than a definitely related government procurement opera-
tion, the government thereby incurs no responsibility nor any obligation
whatsoever; and the fact that the government may have formulated, furnished,
or in any way supplied the said drawings, specifications, or other data is
not to be regarded by implication or otherwise, as in any manner licensing
the holder or any other person or corporation, or conveying any rights or
permission to manufacture, use or sell any patented invention that may in
any way be related thereto.

COLD WELDING RESEARCH FINAL REPORT

BY

D. B. SHELDON

PHILCO-FORD CORPORATION
SPACE AND RE-ENTRY SYSTEMS DIVISION

JANUARY 1970

THIS DOCUMENT IS SUBJECT TO SPECIAL EXPORT CONTROLS, AND EACH TRANS-
MITTAL TO FOREIGN GOVERNMENTS OR FOREIGN NATIONALS MAY BE MADE ONLY
WITH PRIOR APPROVAL OF AFRPL (RPPR/STINFO), EDWARDS, CALIFORNIA 93523.

PREPARED FOR:

AIR FORCE ROCKET PROPULSION LABORATORY
AIR FORCE SYSTEMS COMMAND
EDWARDS AIR FORCE BASE, CALIFORNIA

CONTRACT F04611-68-C-0077

FORWARD

This report (SRS TR-DA2175) describes the activity accomplished on the cold welding research program (Contract F04611-68-C-077) during the period from May 1968 to September 1969. The project was conducted by the Philco-Ford Corporation. The Project Officers were Mr. H. J. Smith and Mr. D. T. Clift. This report was prepared by Philco-Ford, Space and Re-entry Systems Division, Palo Alto, California.

This report has been reviewed and is approved.

D. T. Clift

ABSTRACT

During Phase I of this research, a small experimental contactor was used
to obtain electrical contact resistance data in air and and in vacuum.
These data show that an electronically-pumped vacuum system can effectively
simulate the vacuum of actual space: the contact resistance data obtained
in vacuum was in agreement with contact resistance data obtained from two
small earth satellites. During Phase II, four solenoid valves were tested
in the same electronically-pumped vacuum system used during Phase I; the
test results were compared with adhesion data generated by identical valves
during space flight tests. The contacting surfaces of the valves and the
experimental contactor experienced only normal stresses. In order to
determine the margin before failure existing in each of the valves during
the space flight tests, incrementally increasing stresses were applied to
the valves' sealing surfaces. The results of Phases I and II show that
cold welding in space occurs near or above the yield point of one of the
surfaces. A space-flight qualification test was written.

ACKNOWLEDGMENTS

TABLE OF CONTENTS

LIST OF ILLUSTRATIONS

LIST OF TABLES

SECTION I

SUMMARY

Under certain conditions two metallic surfaces experience adhesion at
temperatures substantially below the melting point of either metal; in
this case the adhesion is referred to as cold welding. It has been
recognized for several years that cold welding is a potential hazard in
space. Phase I of this research, discussed in Ref. 9, demonstrated that
for the purpose of studying cold welding between engineering surfaces,
the ion-pump vacuum system described in Section IV of this report
satisfactorily simulated the space environment. The term "engineering
surface" is used to designate a surface which has been exposed to ambient
atmosphere, but which has not otherwise been contaminated.

During Phase I, a small experimental contactor was used to obtain contact
resistance data in air and in vacuum; these data were used to determine
the suitability of the ion-pumped vacuum system for simulating the vacuum
of actual space. During Phase II, four solenoid valves were tested in
the same ion-pumped system used during Phase I; the test results were
compared with adhesion data generated by identical valves during space
flight tests. The purpose of Phase II was to determine if cold welding
between engineering surfaces can result from simultaneous exposure to the
space environment and relatively high normal stress. Only normal impact
of opposing surfaces was considered in both Phases I and II, slipping was
not considered. The experimental results of Phase II show that for four
different permutations of stainless steel and tungsten carbide surfaces,
cold welding, if it occurs at all, occurs at stresses near or above the
yield point of one of the surfaces. Other data obtained during Phase I
suggest that this result also applies to copper and aluminum.

1

SECTION II

INTRODUCTION

This report is part of a continuing cold welding research program which was initiated by the Air Force Rocket Propulsion Laboratory in 1965. A substantial portion of this program is discussed in other reports (Refs. 1-8). Previous work has included instrumentation design and fabrication, space flight tests, and ground tests in simulated space environments.

The purpose of the space flight tests was to determine the vulnerability of metallic surfaces to cold welding in space. Two identical satellites, ERS-15 and ERS-16, were built by TRW to carry and monitor instrumentation designed to study cold welding. ERS-15 was launched on 19 August 1966, and ERS-16 was launched on 9 June 1966; both space experiments were successful. The experimental devices designed to study cold welding consisted of five solenoid actuator units positioned at the five available apexes of each octahedral satellite. An ejection tube connecting the satellite to its launch canister was attached to each satellite's remaining apex. Of the five actuator units, four were derived from solenoid valves in which different materials combinations were incorporated as the poppet-seat contacts; the fifth actuator unit consisted of eight pairs of 1/8" diameter contacting spheres. The eight contacts were closed simultaneously by a solenoid unit derived from the valves' design; the entire device is referred to as a "supplemental contactor". A photograph and schematic diagram of the type of valve tested are shown in Figs. 1, 2 and 3; a schematic diagram of the supplemental contactor is shown in Fig. 4. The materials employed by each valve are shown in Table 1; the materials employed by the supplemental contactor are shown in Table 2.

The supplemental contactor was designed to provide precise data describing any adhesive force which developed between the contacts during space flight and to relate actual space to various types of space simulation techniques. Each contact consisted of a stationary ball and an opposing ball which impacted on the stationary ball. The contacts were normally open. Adhesive force, if any, was observed by using current integration to measure the time each contact remained closed. The contacting balls were 0.125 ± 0.001" in diameter and made of the following metals: stainless steel, tungsten carbide, aluminum, and copper (see Fig. 4 and Table 2).

The "supplemental contractor experiment" (SCE) was more of a scientific, rather than engineering, experiment since it did not involve specific hardware application. The valves were an actual engineering configuration, testing the interfacial contact characteristics of stainless steels and tungsten carbide while the contractor experiment included aluminum and copper in addition to stainless steel and tungsten carbide. Another comparison should be considered: only four material couples were flown in each space flight through the use of the valves. On the contractor experiment, eight material couples were investigated on each flight. The SCE proved to be an extremely sensitive integrating device for measuring contaminant build-up on a surface due to oxidation, dust, oil-vapor or other sources.

2

Figure 1
Solenoid Valve

INLET

VALVE SEAT

OUTLET

SCALE: 6X ENLARGEMENT

3
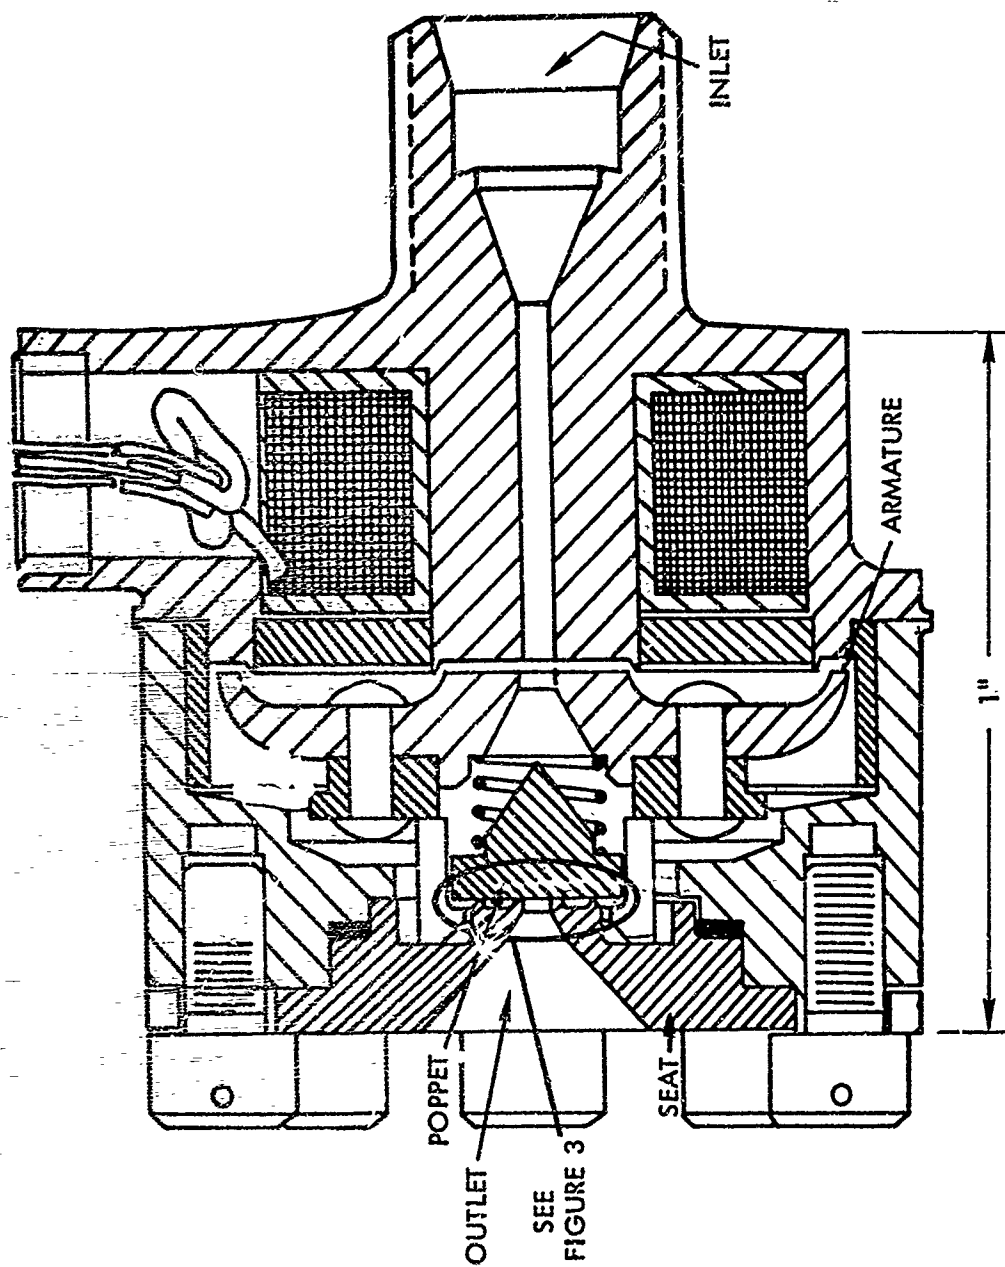
Figure 2
Cross-Section of Solenoid Valve

INLET

ARMATURE

1"

POPPET

OUTLET

SEE
FIGURE 3

SEAT

4

BUMP RING

.001"

SEAT

LAND .006" WIDTH

SURFACE FINISH & OTHER
CHARACTERISTICS GIVEN IN REFERENCE 4.

POPPET

TYPICAL DIMENSIONS

OUTLET

PORT DIA
.040"

SEAT

LIFT OFF

.003"

5
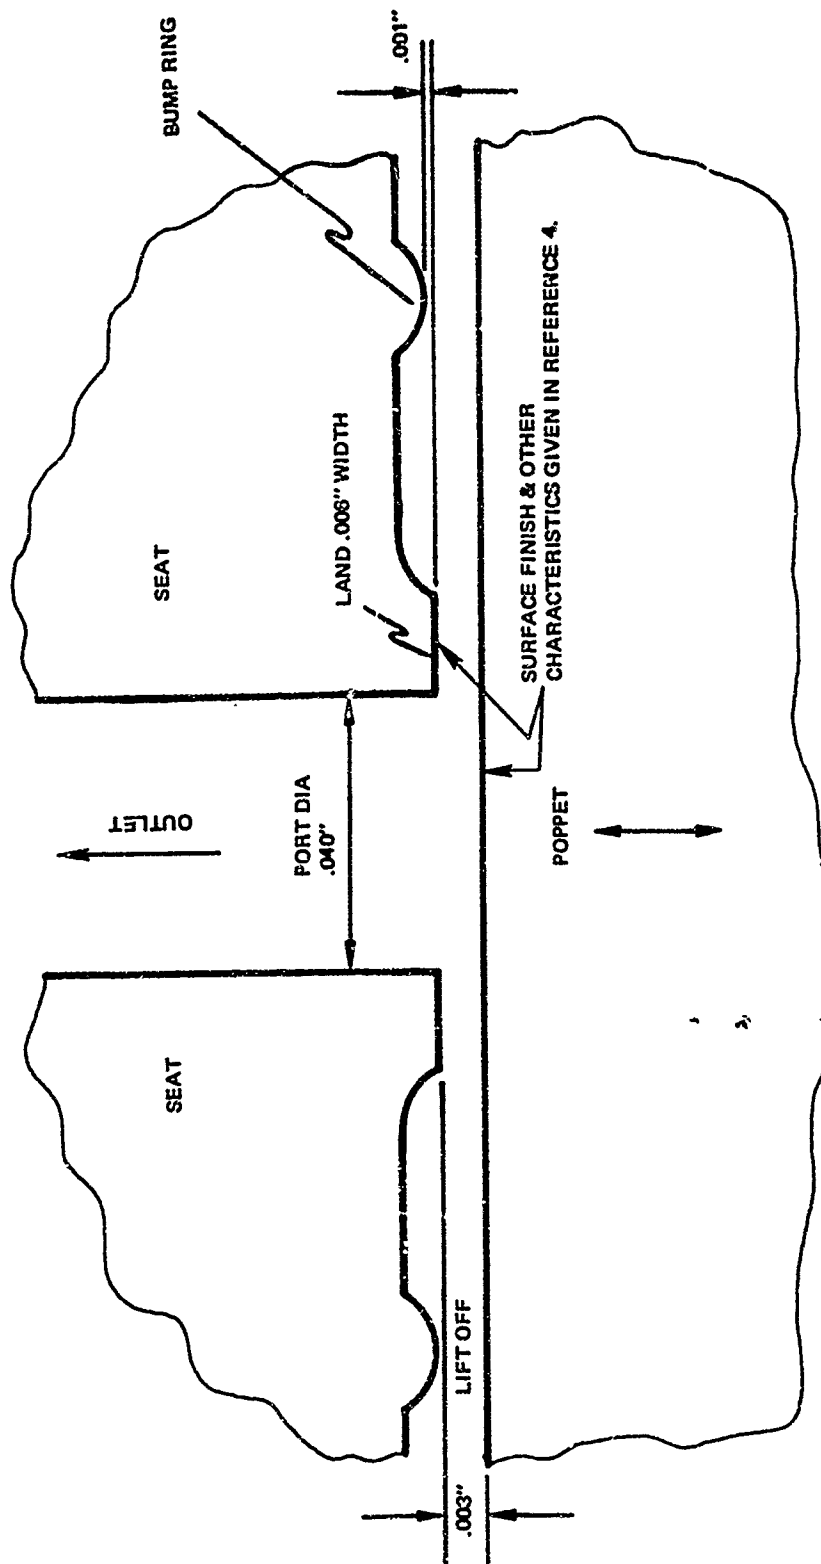
Figure 3
Solenoid Valve Seat Detail

TABLE 1

SOLENOID VALVE MATERIALS

VALVE NO.	MATERIALS	PARKER-HANNIFIN CORP.	SERIAL NO.
V_1	440C x 17-4 PH	5650004	B520003
V_2	17-4 PH x WC	5650005	B520103
V_3	440C x WC	5650006	B52023
V_4	WC x WC	5650007	B520303

MATERIAL IDENTIFICATION

440C - Stainless Steel
17-4 PH - Stainless Steel
WC - Tungsten Carbide

6

ACTUATOR

SPRING

CONTACT UPPER

CONTACT FIXED

ARMATURE

1"
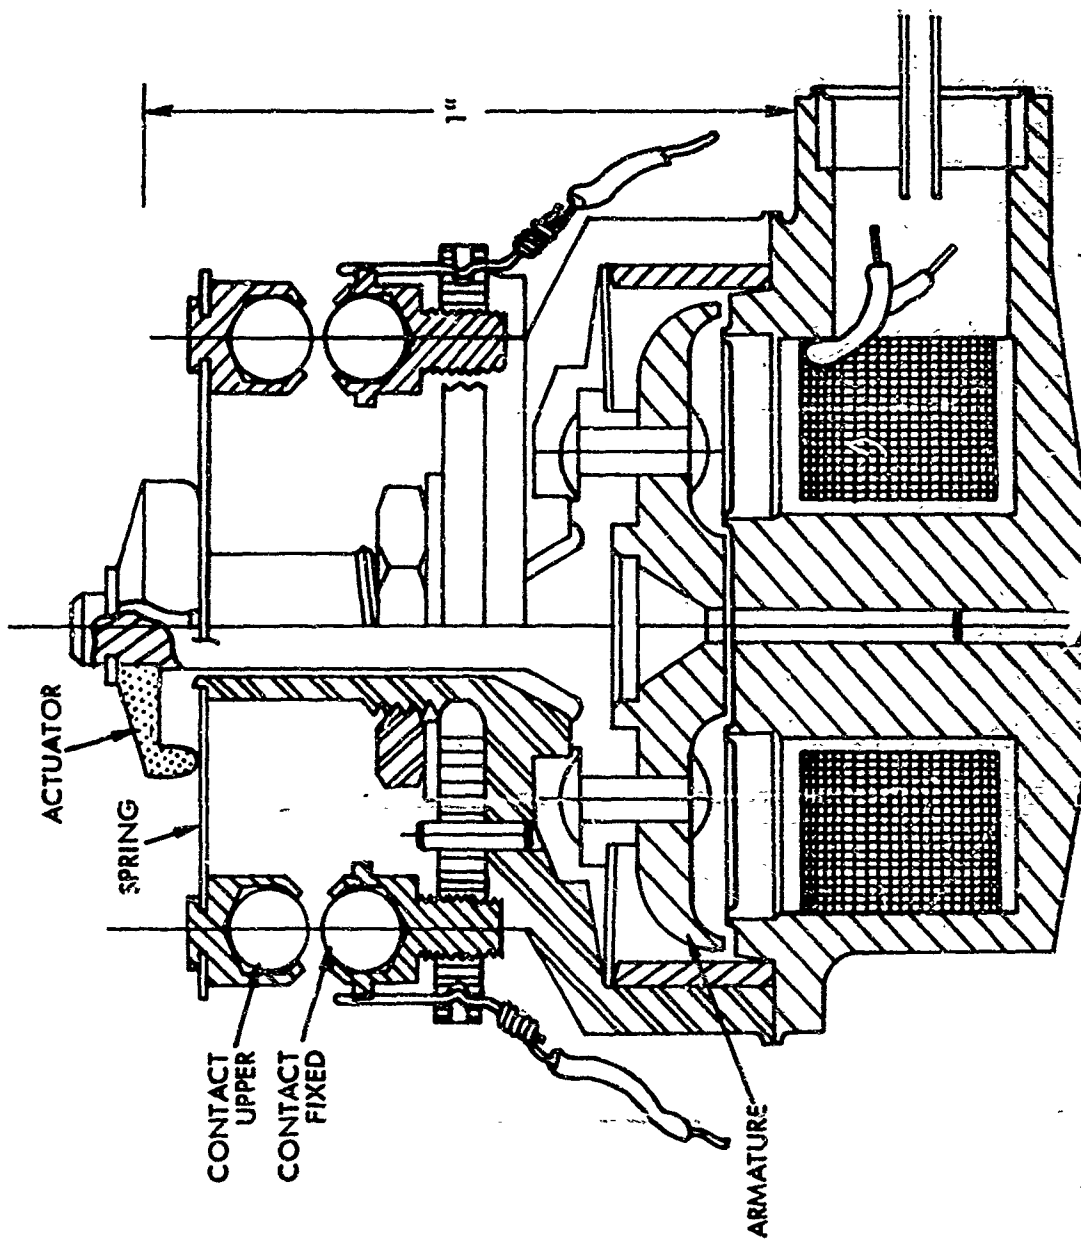
Figure 4

Cross-Section of Supplemental Contactor

7

COPPER VACUUM GASKET

HOLDING FIXTURE FOR
ROTATING SUPPLEMENTAL CONTACTOR

SUPPLEMENTAL CONTACTOR ASSEMBLY

EIGHT CONTACT EXPOSED TO VACUUM

Figure 5

Supplemental Contactor

8

TABLE 2

TEST SUPPLEMENTAL CONTACTOR BALL ARRANGEMENT
Supplemental Contactor S/N B520406 (normally open)

Contact S_1	-	17-4 PH on 17-4 PH
Contact S_2	-	WC on WC
Contact S_3	-	2014-0 on 2014-0
Contact S_4	-	OFHC on OFHC
Contact S_5	-	440C on 2014-0
Contact S_6	-	440C on OFHC
Contact S_7	-	17-4 PH on 2014-0
Contact S_8	-	17-4 PH on OFHC

MATERIAL IDENTIFICATION

440C	-	Stainless Steel
17-4PH	-	Stainless Steel
WC	-	Tungsten Carbide
2014-0	-	Aluminum
OFHC	-	Oxygen Free High Conductivity Copper

For both of the space experiments, the SCE was cleaned and calibrated during pre-launch preparations. In both cases, the contractor experiment was exposed to sea level atmospheric conditions for more than a week prior to launch; this surface oxidation/contamination was evident during initial data acquisition of both launches. On both flights, the majority of the contracts "cleaned-up" after a brief exposure in space.

The most significant aspect of the current program is that, in the electronically pumped vacuum, the contacts "cleaned up" much the same as they did in space. Therefore, the SCE provided an extremely beneficial measurement of the adequacy of space-simulators.

The four solenoid valves on each satellite were intended to provide data describing the adhesive force which developed between surfaces employed in a typical engineering configuration. Permutations of stainless steel and tungsten carbide were incorporated as the poppet-seat contacts of each of the four solenoid valves (see Figs. 1, 2 and 3 and Table 2). The valves were normally closed. Prior to the flight experiments it was expected that most soft metals would experience some cold welding in space; as a result, two very hard metals were selected to form the poppet-seat interface. Ground tests showed that softer metals are more likely to experience cold welding than hard metals (Ref. 3). Therefore, hard metals were regarded as candidate materials for the suppression of adhesion in space applications requiring metallic contact.

Unexpected results were obtained from both the two satellites and instrumentation located inside environmental chambers employing oil diffusion pumps. No definite adhesion was observed to occur either in space or the simulation chambers, and contact resistance data obtained in space by the supplemental contactor was significantly different from corresponding data obtained using space simulation chambers. The flight data indicated that the contacts' resistances decreased as a result of exposure to the space environment. Pre-flight data obtained from space simulators employing oil diffusion pumps did not indicate a decrease in contact resistance; in fact, contact resistance data obtained using these space simulation chambers showed a greater increase than that observed in ambient air.

In view of the questionable results obtained using oil diffusion pumps, Phase I of the present research was initiated; and it was decided to evaluate an ion pump's capability of simulating surface conditions in space. This evaluation was performed using the same supplemental contactor which was utilized during the oil diffusion pump tests; complete details are given in Cold Welding Research Phase I Report, AFRPL-TR-68-211. The contact resistance of each of the eight contacts of the supplemental contactor was substantially reduced after the pressure in the vacuum system described in Section IV of this report was lowered from atmospheric pressure to approximately 10^{-8} torr.

In addition to high vacuum, ultraviolet radiation was used to simulate the space environment. Ultraviolet radiation at approximately one earth sun intensity did not effect a further reduction of the contacts' resistances. Extended duration tests, up to 70 hours, were performed using the supplemental contactor. The purpose of these tests was to determine if cold welding of any of the eight contacts would occur. An analytical study was also performed to determine the approximate values of the contacts' impact

stresses; it was assumed that the response of the contacts was entirely elastic. This information provided a basis for evaluating the extended duration test data. The velocity of impact was determined from high-speed motion pictures.

The copper-copper contact was observed to cold weld in vacuum; momentary adhesion of 17-4 PH stainless steel and copper contact was also observed. The results of the analytical study showed that the impact stresses of all contacts were high enough to deform the substrate which supports the oxide layer. The analysis also showed that the copper-copper contact experienced the highest ratio of impact stress to yield stress, and that the 17-4 PH stainless steel on copper contact experienced the next highest ratio of impact stress to yield stress. This suggests that the ratio of impact stress to yield stress of contacting engineering surfaces in vacuum or space may be an important dimensionless parameter. The above results were obtained during Phase I.

Phase II consisted of testing four solenoid valves whose configuration is typical of the design used in space vehicles. Testing was performed in the same chamber used during Phase I. The poppet-seat interface of each solenoid valve was subjected to increasingly severe applications of increased stress. This was done in vacuum ($p\sim10^{-8}$ torr). The purpose of applying the increased seating stresses was to determine if the valve's poppet or seat deform prior to the occurrence of cold welding. Deformation of a valve's sealing surfaces was indicated by an increased gas leakage rate. The valves' leakage rates were measured when the valves were outside the vacuum system. Cold welding was indicated by sticking at the poppet-seat interface immediately after the application and removal of increased seating stress. After failure, whetherby cold welding or increased leakage, each valve's poppet and seat were examined with a microscope and an interference profilometer. These inspections served to determine the extent of deformation of the sealing surfaces.

11

SECTION III

THE RESULTS OF PHASE I

III.1 SUMMARY OF PHASE I

Several tests were performed using the supplemental contactor described in AFRPL Report No. AFRPL-TR-67-1 (AD 380181). These tests included measuring the change in contact resistance of each of the eight pairs of contacts mounted on the supplemental contactor as the supplemental contactor was exposed to a series of different environments. These different environments were air, vacuum (p = 10^{-8} torr), and vacuum in combination with ultraviolet radiation. The test chamber was evacuated by means of ion, sublimation and cryogenic pumps. Slow motion movies of the supplemental contactor's actuation stroke were made; the camera speed was usually faster than 2300 frames per second. The velocities of impact of the contacts were obtained from these movies. Approximate values for the stresses and areas at the contacts' interfaces were obtained by using the theory of elastic deformation.

The experimental results showed that an ion-pumped vacuum system can be successfully employed to remove contaminants which would otherwise lower the probability of successful electrical contact. The results of the analytical study showed that the impact forces of the contacts were high enough to deform the substrate which supports the surface oxide layer.

One case of cold welding was observed in vacuum. The contact involved in the cold welding observation was copper on copper. Adhesion of the stainless steel and copper contact was also observed. The analysis showed that the copper on copper couple experienced the highest ratio of impact stress to yield stress. This suggests that the ratio of impact stress to yield stress of contacting engineering surfaces in vacuum or space may be an important dimensionless parameter. An "engineering surface" is considered to be a surface which has been exposed to the atmosphere, but has not been otherwise contaminated.

The behavior of the contacts in air was somewhat erratic with the general trend being that the majority of the contacts became more contaminated. The data usually followed a stochastic pattern. Successful electrical contact was accomplished with nearly 100 percent reliability when the contactor was in vacuum. Some changes in the contact resistances occurred in vacuum after several hours of testing. Exposing the contactor to ultraviolet radiation did not affect the data. When the contactor was tested in air at temperatures above approximately $100^{\circ}F$, there was an apparent increase in contact resistances. Identical results were obtained in vacuum. This observed increase was probably due, at least to some extent, to the increasing resistance of the contactor's solenoid coil as the temperature of the coil rose along with the ambient temperature.

III.2   THE CONTACT RESISTANCE MEASUREMENTS

Phase I consisted of testing eight metallic contacts which were closed by
a common solenoid. The eight contacts are mounted on a platform attached
to a magnetic solenoid. The entire unit, consisting of the contacts, the
platform, and the solenoid was referred to as the "supplemental contactor"
or simply "the contactor". A detailed description of the design and opera-
tion of the supplemental contactor is given in Ref. 4. Each of the metallic
contacts consisted of a pair of 1/8" diameter metal balls. The data obtained
during Phase I was used to compare the performance of ion and oil diffusion
pump vacuum systems. A decrease in electrical contact resistance as the
ambient pressure was lowered from one atmosphere to below 10^{-6} torr was
regarded as a favorable index of performance. Data describing the performance
of an ion-pump vacuum system was generated by the present project; data
obtained using a diffusion-pump vacuum system is available in Ref. 4. The
data obtained using a diffusion-pump vacuum system indicates that this
type of system did not effectively reduce contact resistance as the pres-
sure was reduced several decades below 1 atmosphere. The vacuum system
which was utilized during the present work was effective in substantially
reducing contact resistance. The contact resistances of the supplemental
contactor were first studied in air at temperatures near $32^{\circ}F$, $70^{\circ}F$, and
$120^{\circ}F$. Later the contactor's contact resistances were studied near room
temperature in vacuum ($r = 10^{-8}$ torr) and in a combined vacuum and ultra-
violet radiation environment. The manifestation of cold welding (or any
metal-to-metal adhesion effect), if it occurred between two contacts, was
discovered from visual examination and interpretation of this data.

The stress/strain conditions of the contacts over their area of impact
were studied. The stress/strain conditions of each contact pair at its
operational impact velocity was examined.

III.2.1 Experimental Apparatus

The experimental apparatus consisted primarily of a supplemental contactor,
miscellaneous supporting equipment required to monitor and control the
supplemental contactor, an ion-pump vacuum system, an ultraviolet lamp,
and photographic equipment. Each of these items will be described indi-
vidually.

III.2.1.1 Supplemental Contactor

The following three supplemental contactors were available for testing:

                    No. S/N B520404
                    No. S/N B520405
                    No. S/N B520406

13

Only one supplemental contactor, Serial Number S/N B520406, was tested during Phase I. This contactor previously received 72,000 actuations in a diffusion-pump vacuum system at TRW. A photograph of the supplemental contactor in its holding fixture is shown in Fig. 5. Each contact consisted of a stationary ball and an opposing ball which impacts on the stationary ball. The contacting balls were 0.125 ± 0.001 inches in diameter and are made of the following metals: stainless steel, tungsten carbide, aluminum, and copper. The exact arrangement of the balls is shown in Table 2. The contacts were normally open; each contact was closed simultaneously by a single solenoid. Mechanical motion was transmitted from the solenoid plunger to each of the movable balls by a flat copper-beryllium spring. In Fig. 5 this flat spring can be seen extending from under a white boron nitride disk to the brass sockets holding the movable balls. An electronics package built at TRW was used to regulate the frequency of actuation; three actuation frequencies were available. The electronics package was also used to generate an output voltage signal which was an indication of the amount of charge passing through a contact during each actuation cycle. The voltage output of the electronics package was monitored by a recorder. The recorder readings were normalized with respect to a short circuit condition achieved by manually depressing a contact.

Sample contactor data is shown in Figs. 6 and 7. This data was taken directly from a pin recorder (see Paragraph III.2.1.2. The data comes off the recorder from right to left. In Fig. 6 none of the contacts is making successful electrical contact.

Figure 6

Supplemental Contactor Data: No Contacts Making Successful Electrical Contact

14

In Fig. 7 all of the contacts are making successful electrical contact; the data were obtained from one of the vacuum tests. The numbers on Figs. 6 and 7 indicate the contact numbers corresponding to the position of the voltage pulses. The groups of four large pulses are not associated with the contactor data; however, they do serve to identify the voltage pulses. For example, the pulse associated witn contact No. 1 immediately precedes each group of four large pulses. Fig. 8 shows the result of manually short circuiting contact No. 7. The appearance of such a pulse during an actual test is indicative of cold welding. The appearance of a pulse whose height is only slightly greater than the pulses shown in Fig. 7 is indicative of temporary adhesion.
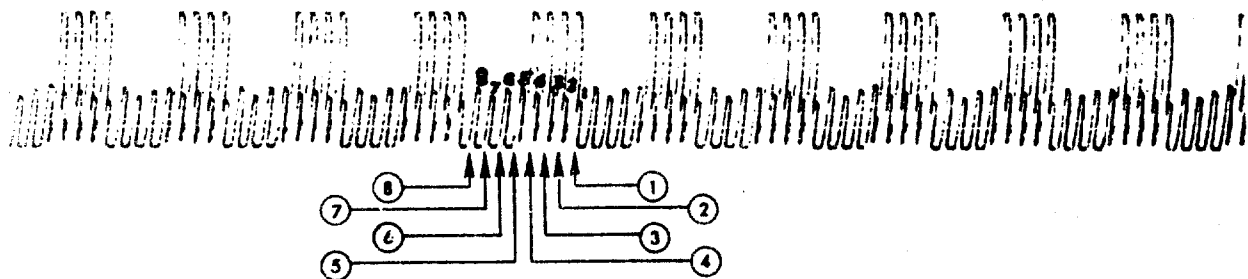

Figure 7

Supplemental Contactor Data: All Contacts Making Successful Electrical Contact
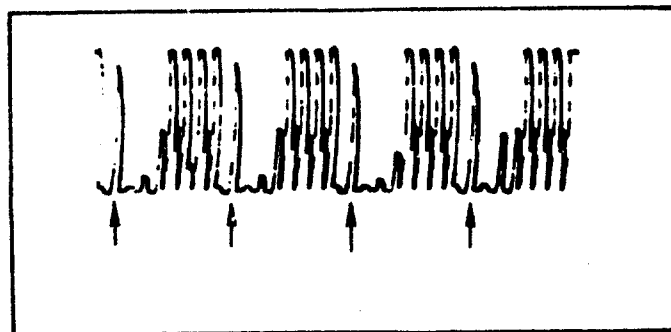

Figure 8

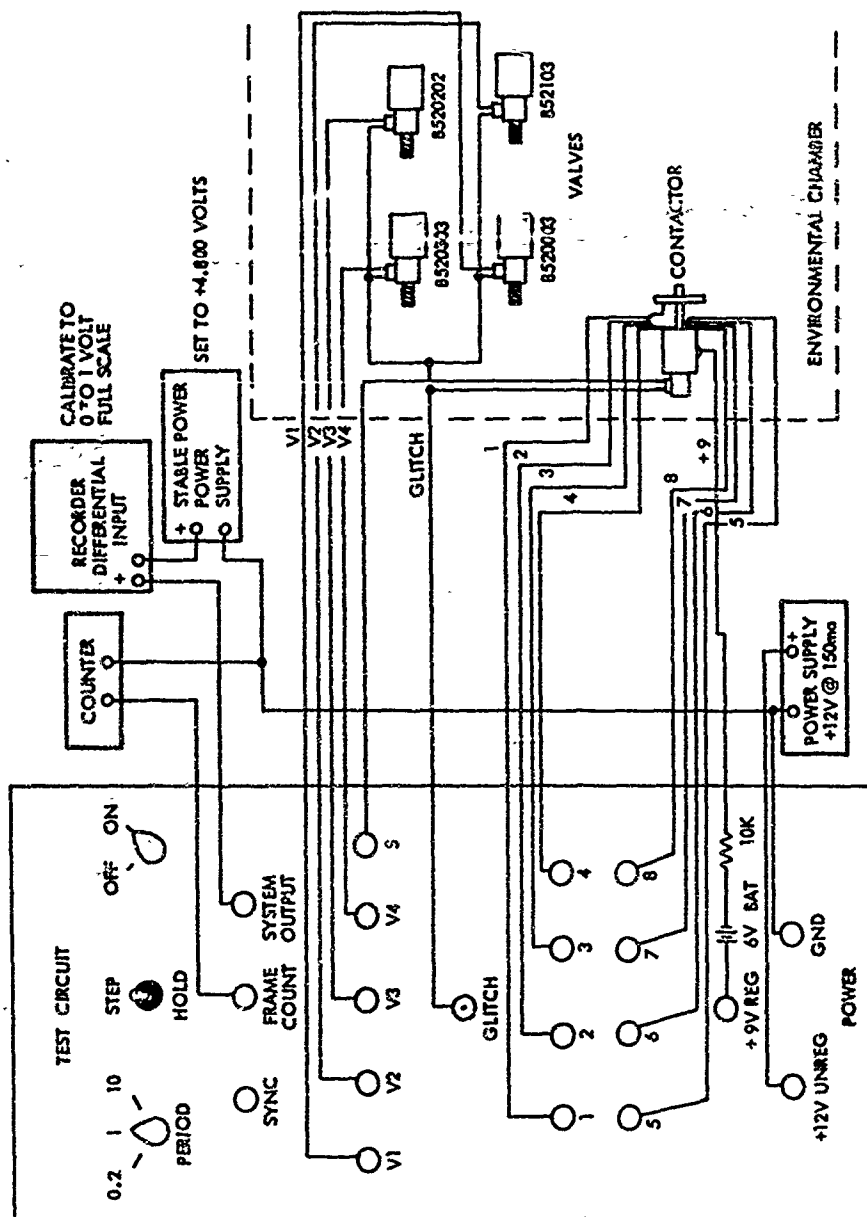Supplemental Contactor Data: Manual Short-Circuiting

15

Figure 9

Block Diagram of Cold Welding Experiment

III.2.1.2 Supporting Equipment

The circuit diagram describing how the supplemental contactor was monitored and controlled is shown in Fig. 9. The terminals VI through V4 were not connected to any valves during Phase I. The test circuit was built by TRW. The counter was a Computer Measurements Company frequency-period counter (Model No. 201B); the recorder was a Beckman RS Dynograph recorder; the stable power supply was a Hewlett Packard power supply (Model No. 721); and the 12-volt power supply was fabricated in the laboratory. A Missimers combination oven and refrigerator (Model FT1.5-120x350) was used to control the temperature of the supplemental contactor during the tests in air at $32^{\circ}F$, $80^{\circ}F$, $120^{\circ}F$, and $150^{\circ}F$.

III.2.1.3 Vacuum System and Related Equipment

The supplemental contactor was tested in a vacuum system at a pressure of approximately 10^{-8} torr. An AH-6 ultraviolet lamp was used to simulate solar U.V. radiation during some of these tests. This section describes the vacuum system, the contactor holding fixture, and the AH-6 lamp.

III.2.1.3.1 Vacuum System

The vacuum system (Fig. 10) consisted primarily of a Varian VI-260 vacuum system. An 18" diameter stainless steel bell jar was sealed to the original VI-260 system by means of a copper gasket. The pumps used in the VI-260 vacuum system are as follows:

1. One 500 1/s VacIon pump and control unit (Varian Model 921-0038)

2. One 8000 1/s titanium sublimation pump (Varian Model 922-0032)

3. Three VacSorb $78^{\circ}K$ cyrogenically activated roughing pumps

All pressure measurements were made using a nude ion gauge (Varian No. 971-5008). With the exception of one completely dry rubber O-ring in the ion pump isolation valve, the vacuum system was all metal. The single remaining O-ring could have been removed but this would have introduced additional contamination. Without use of the ion pump isolation valve, it would not have been possible to prevent air at a pressure of one atmosphere from entering the ion pump. The contaminates contained in this air would have been re-emitted into the test chamber during a test. Initial favorable test data obviated removal of the O-ring in the isolation valve.

III.2.1.3.2 Supplemental Contactor Holding Fixture

The supplemental contactor holding fixture is shown in Figs. 5 and 11. The necessary contactor electrical leads and two copper-constantan thermocouples were introduced into the vacuum system through two 2-3/4" O.D. Conflat flanges. The contactor supporting tube was made of 304 stainless steel and
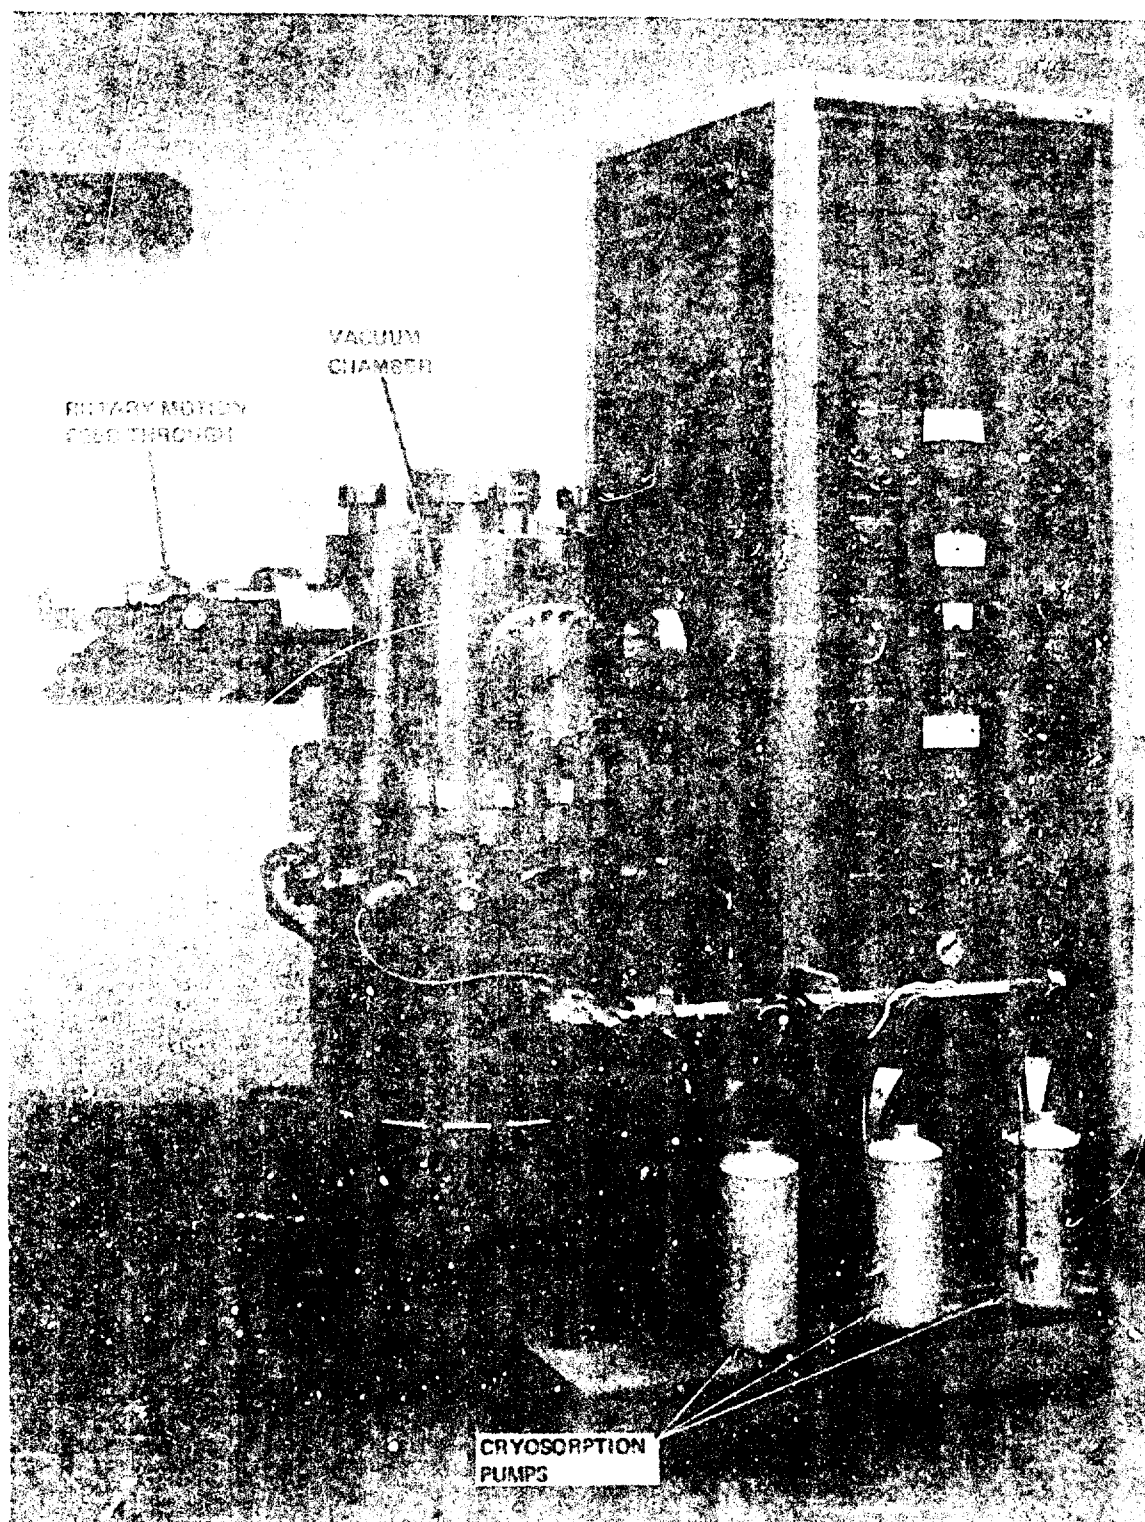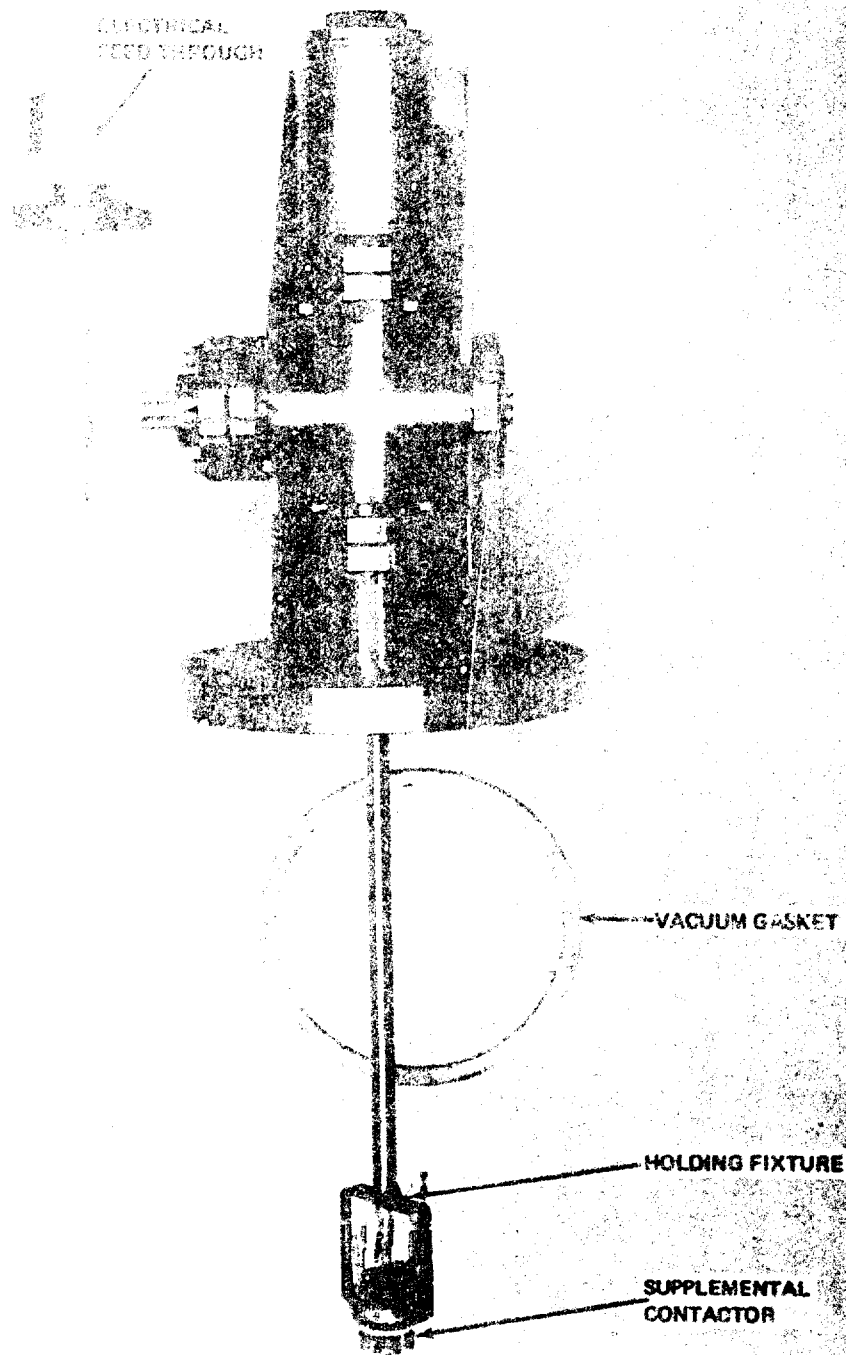
Figure 10

Vacuum System

ELECTRICAL
FEED THROUGH

VACUUM GASKET

HOLDING FIXTURE

SUPPLEMENTAL
CONTACTOR

Figure 11

Supplemental Contactor Holding Fixture

19

the insulation of the contactor lead wires was ⸱ ⸱ of fiberglass. (The insulation shown in Figs. 5 and 11 is Teflon.) ⸱e large flange is a 3" O.D. Varian Conflat flange; the flange's copp⸱ ⸱ sealing gasket is also shown in the figures. The rotary motion feedth⸱ ⸱gh device, Varian Model No. 954-5026, is shown at the top of Fig. 11. ⸱ ⸱s unit does not penetrate the wall of the vacuum system; motion was trans⸱ ⸱ted into the interior of the system by means of magnets. The rotary mo⸱ ⸱n feedthrough was driven by a 1/12 RPH Haydon timing motor (Model No. ⸱ ⸱50). This motor was activated only during the tests involving the ⸱ ⸱e of ultraviolet radiation; in this case only, it was necessary to ⸱⸱⸱ate the main body of the contactor to insure uniform irradiation of the individual contacts.

III.2.1.3.3 Ultraviolet Simulation Equipment

The ultraviolet simulation equipment is shown in Fig. 13. The upright object is a Kovar and Quartz finger that ext⸱ ⸱ds sideways into the vacuum system. The AH-6 mercury lamp, which remains external to the vacuum system, is shown in the foreground. This lamp is wa⸱ ⸱r cooled. Fig. 12 shows a comparison of Johnson's solar radiation cur⸱ ⸱ and a typical spectrum of the AH-6. As seen from the contactor, the w⸱ ⸱er jacketed AH-6 lamp without filtering provides a source intensity equi⸱⸱⸱ ent to about 3 earth suns. During the experimental tests the output of ⸱ he AH-6 lamp was attenuated by a neutral density filter to an intensit⸱ ⸱f about three quarters of an earth sun. It was necesary to use this fil⸱ ⸱r in order to avoid overheating the contactor.
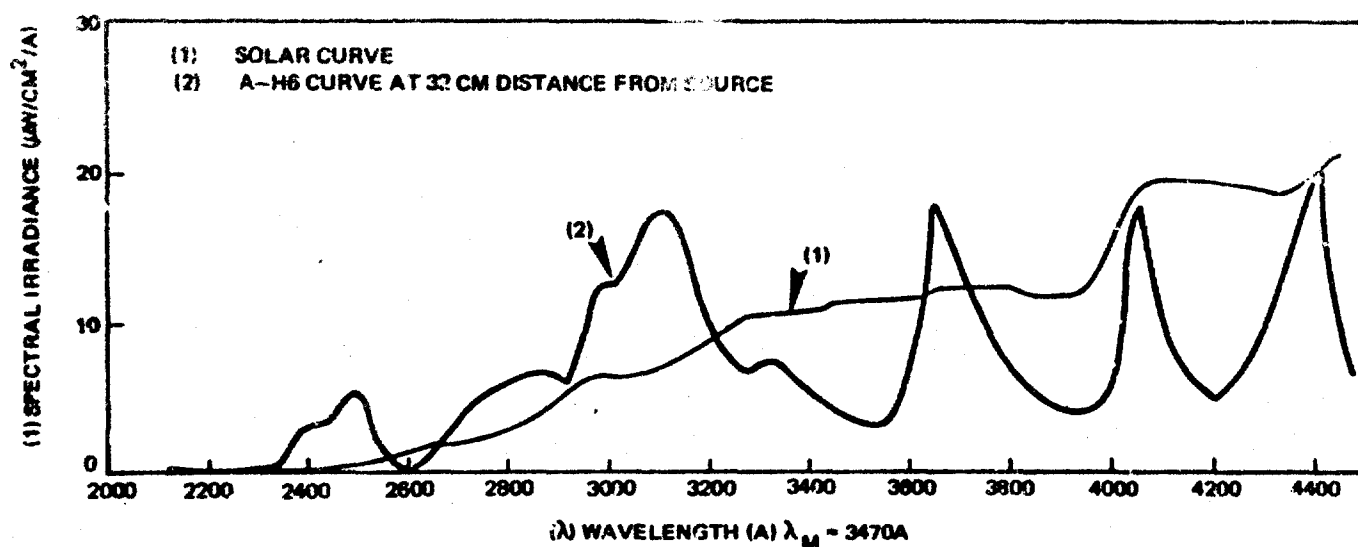

Figure 12

Spectral Energy Districution of A-H6 Lamp and Sunlight
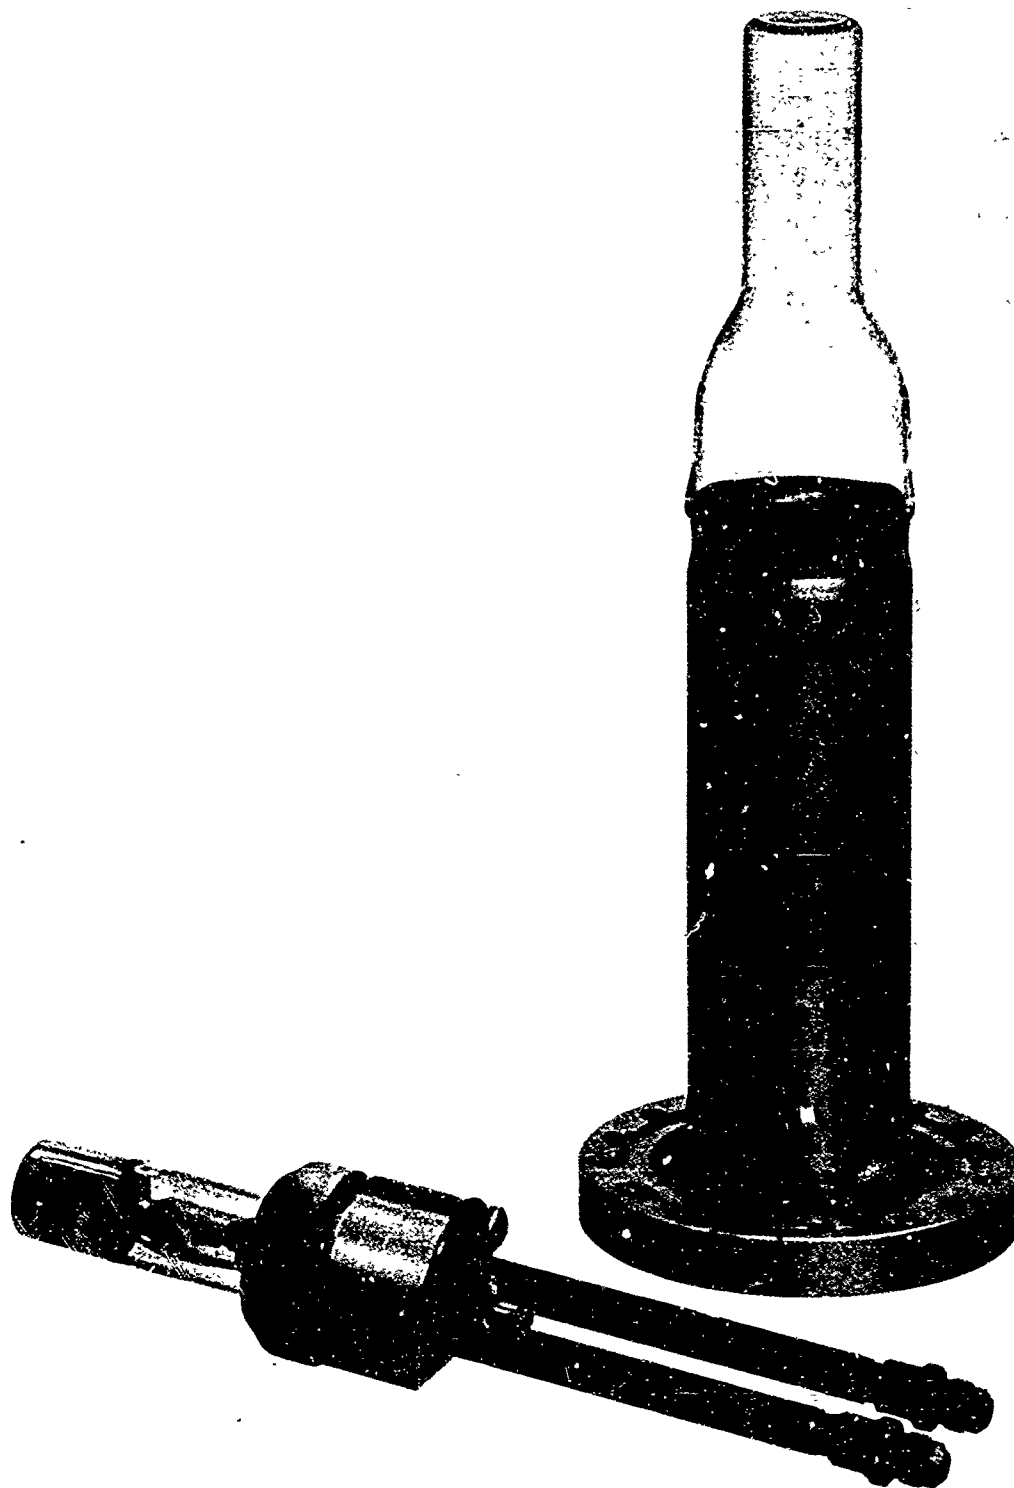
(From GE Bulletin F-N412, 402M4-57)

20

Figure 13
Ultraviolet Radiation Equipment

21

SECTION IV

EXPERIMENTAL APPARATUS

IV.1   VACUUM SYSTEM

The vacuum system (Fig. 10) has already been described in Section III.2.1.3.1.

IV.2   SOLENOID VALVES

The solenoid valves were of the type P/N 565003 manufactured by the Parker-Hannifin Corporation. The actuation of the valves was controlled bv an test circuit built by TRW. Different material combinations were incorporated as the seat-poppet contacts of each of the four solenoid valves (see Table 1). These four combinations of engineering metals were employed in a typical engineering configuration. The body of the valve unit was modified to permit a maximum vacuum exposure of the test surfaces; the test materials were self-shielded from radiation (see Figs. 1 and 2). In order to apply increased seating stresses, the diameter of the central canal behind the poppet was increased to 0.125". In space, similar valves were cycled periodically from a normally closed position, opening for 70 ms every five minutes, over a minimum of six months except for brief eclipse periods. A change in the monitored dynamic opening response of each valve unit served as the means to detect cold welding. A large line-of-sight included angle was provided to the vicinity of the test materials. In this manner, the vacuum level experienced by the metal contacts was not conductance limited.

Observation of a change in valve response characteristics was accomplished through a circuit designed to monitor the solenoid coil current. This is possible since the solenoid current-time waveform is influenced by the mechanical compliance of the device. For illustrative purposes, a typical solenoid valve current waveform is shown in Fig. 14. Referring to Fig. 14,
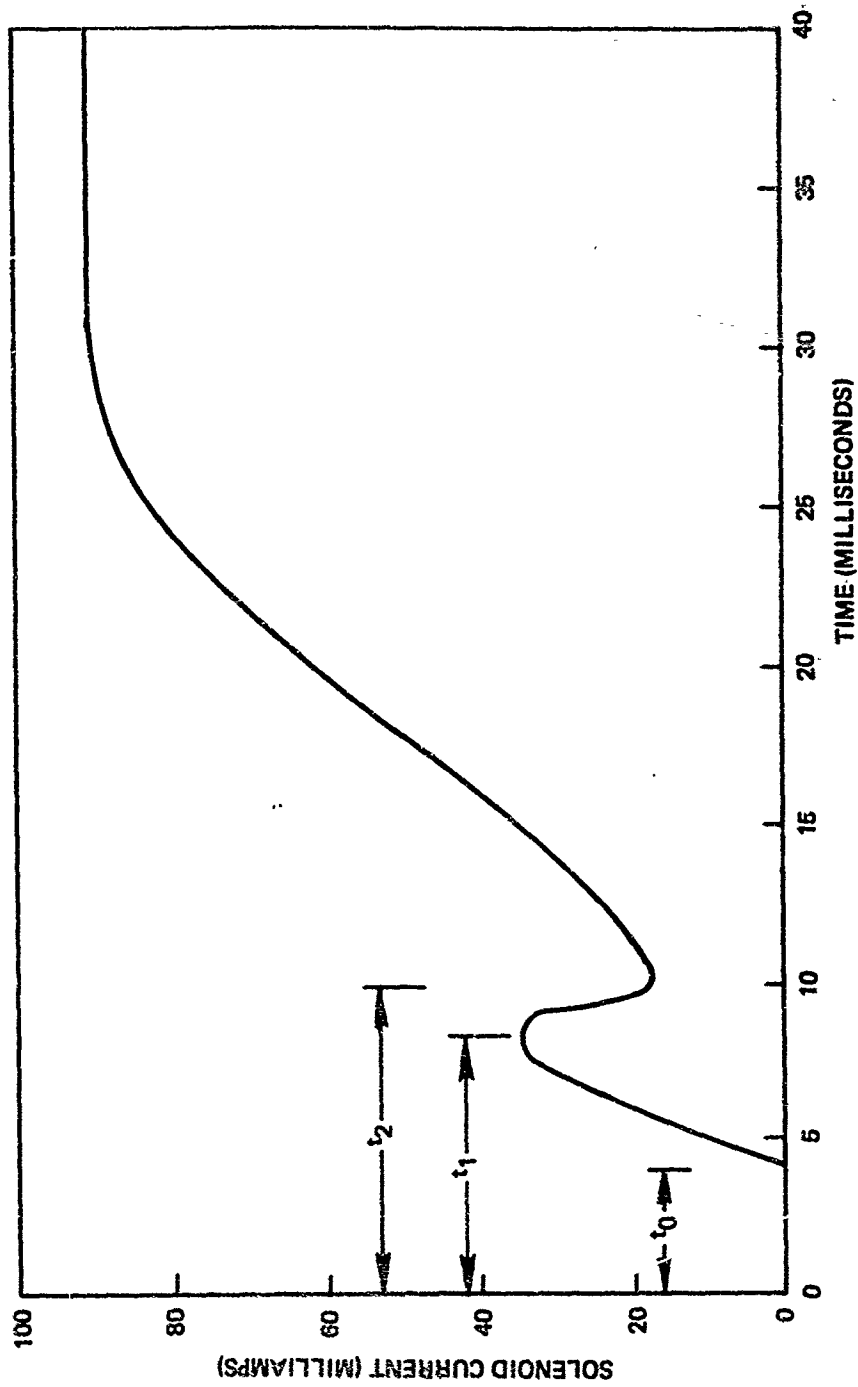
22

Figure 14
Normal Solenoid Current Waveform (Valve No B520103)

23

t_0 represents the application of power to the solenoid coil which starts to saturate; at t_1 the poppet starts to move generating a back emf causing the observed inflection point at t_1. The current trace continues to fall until the poppet-armature has stopped, t_2; at which time the second inflection point occurs and the current continues to saturate. The time between t_0 and t_2 represents the valve response time. The shape and characteristics of the curve are proportional to the coil-armature characteristics, spring forces, and cold welding. In the absence of cold welding, constant spring forces are the dominant factor. Increased breakway forces at the seat-poppet due to cold welding are reflected in a proportional change in the time interval t_0 - t_1; t_1 - t_2 might change with sliding or moving friction. Interpretation of the cold welding forces relies upon sustaining constant solenoid coil characteristics and mechanical spring forces; thus, changes noted in the valve response characteristics will be proportional to cold welding and/or friction. Through calibration, (see Section V.2), the change in (t_2 - t_0) can be related directly to forces at the seat-poppet interface of each valve.

IV.3 PNEUMATIC SYSTEM AND INCREASED STRESS APPLICATOR

A pneumatic system was employed to regulate the application of the increased seating stresses. This system permitted the required forces to be applied smoothly without overshoot. As shown in Fig.15, the pneumatic system applied force to a stress applicator rod. This rod was 0.120" in diameter; the applied force was determined from a strain gauge load cell attached to the rod. Motion was transmitted into the vacuum system by a ½" I.D. stainless steel bellows. The rod applied stress directly to the rear of the poppet. An assembled and disassembled view of the testing configuration is shown in Figs. 16 and 17. These photographs show the valve, its holding fixture, the load cell, the stress applicator rod, a vacuum flange, and a tube leading to the pneumatic system. The bellows is contained in the large cylinder attached to the flange. The principal components of the pneumatic system were: an anaroid manostat, a mechanical vacuum pump, two solenoid control valves, a cylinder of compressed nitrogen gas, and a precision pressure gauge. These components were interconnected by ¼" I.D. stainless steel tubing. The operation of the pneumatic system was sequenced by the Test Circuit.

The aneroid manostat (Wallace and Tiernan Model No. FA-149) was a precision pressure regulator designed to be used in the range 0.8 to 60 inches of Hg (absolute); its precision was ± 0.02 inches of Hg. The nominal I.D. of the two ASCO solenoid control valves was ¼". A Welch mechanical vacuum pump was used in conjunction with the aneroid manostat and also to permit the bellows to return to their neutral position; the capacity of the mechanical pump was 1.40 CFM, and its ultimate pressure was less than 10 microns. When the pneumatic system's internal pressure did not exceed 100 mm of Hg (absolute), a 0-100 mm Hg Wallace and Tiernan diaphram gauge was used to monitor the pressure applied to the bellows.
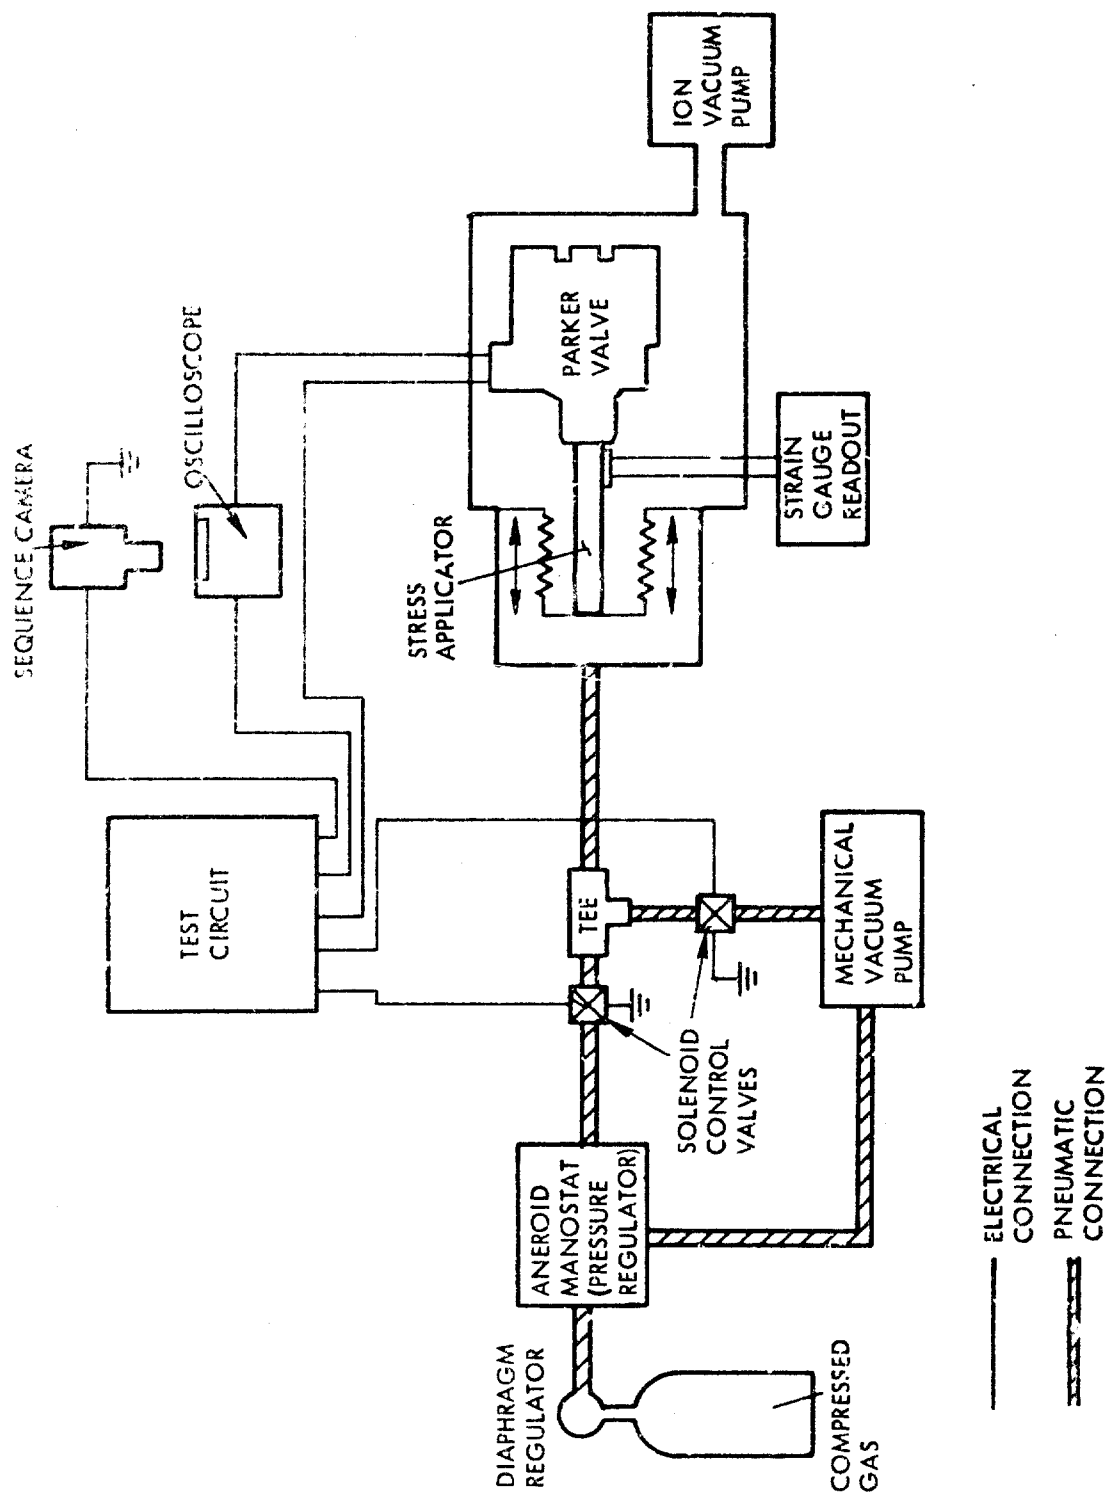
Figure 15

General Schematic Diagram

25

PNEUMATIC LEAD INTO BELLOWS

ADAPTER FOR HOLDING TEST VALVE

STRAIN GAUGE LEADS

LOAD CELL

TEST VALVE

OUTLET
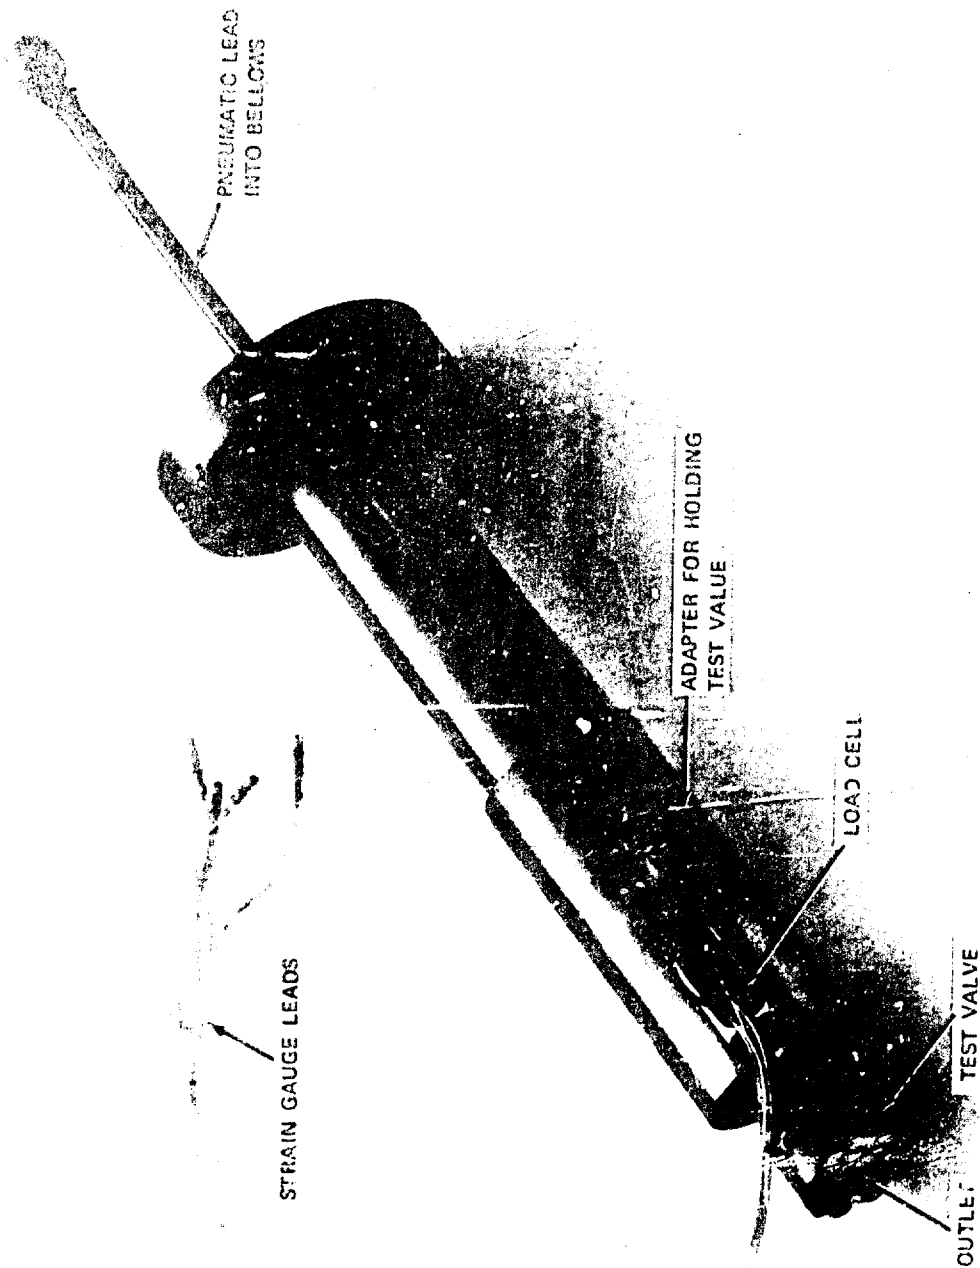
Figure 16

Assembled View of Valves' Holding Fixture

26

PNEUMATIC LOAD INTO BELLOWS

STRAIN GAUGE LEADS

LOAD CELL

0.120" DIAMETER ROD FOR INCREASING
FORCE ON VALVE SEAT

ADAPTER FOR HOLDING TEST VALVE

TEST VALVE (ONE OF FOUR TESTED)

Figure 17

Disassembled View of the Valves' Holding Fixture

IV.4   RECORDING SYSTEM

An automatic recording system was used to monitor the solenoid current
waveform of each Parker valve when the valve was actuated. The valves
were actuated after the increased seating stress was removed. Any indica-
tion of sticking at the poppet-seat interface was indicated by an increase
in a valve's opening time. The opening time, $t_0 - t_1$, was obtained from
the valve's solenoid current waveform as explained in Subsection IV.2.
The principal components of the recording system were a Tektronix 535-A
oscilloscope, including a 1A7 differential amplifier; and a 16 mm Bell and
Howell movie camera.

The movie camera was operated as a sequence camera; each solenoid current
waveform displayed on the oscilloscope was photographed on one frame of
movie film. A valve's solenoid current waveform was observed by measuring
the voltage across a one ohm resistor in series with the valve's solenoid
coil. A 10X probe was attached to each side of the one ohm resistor; the
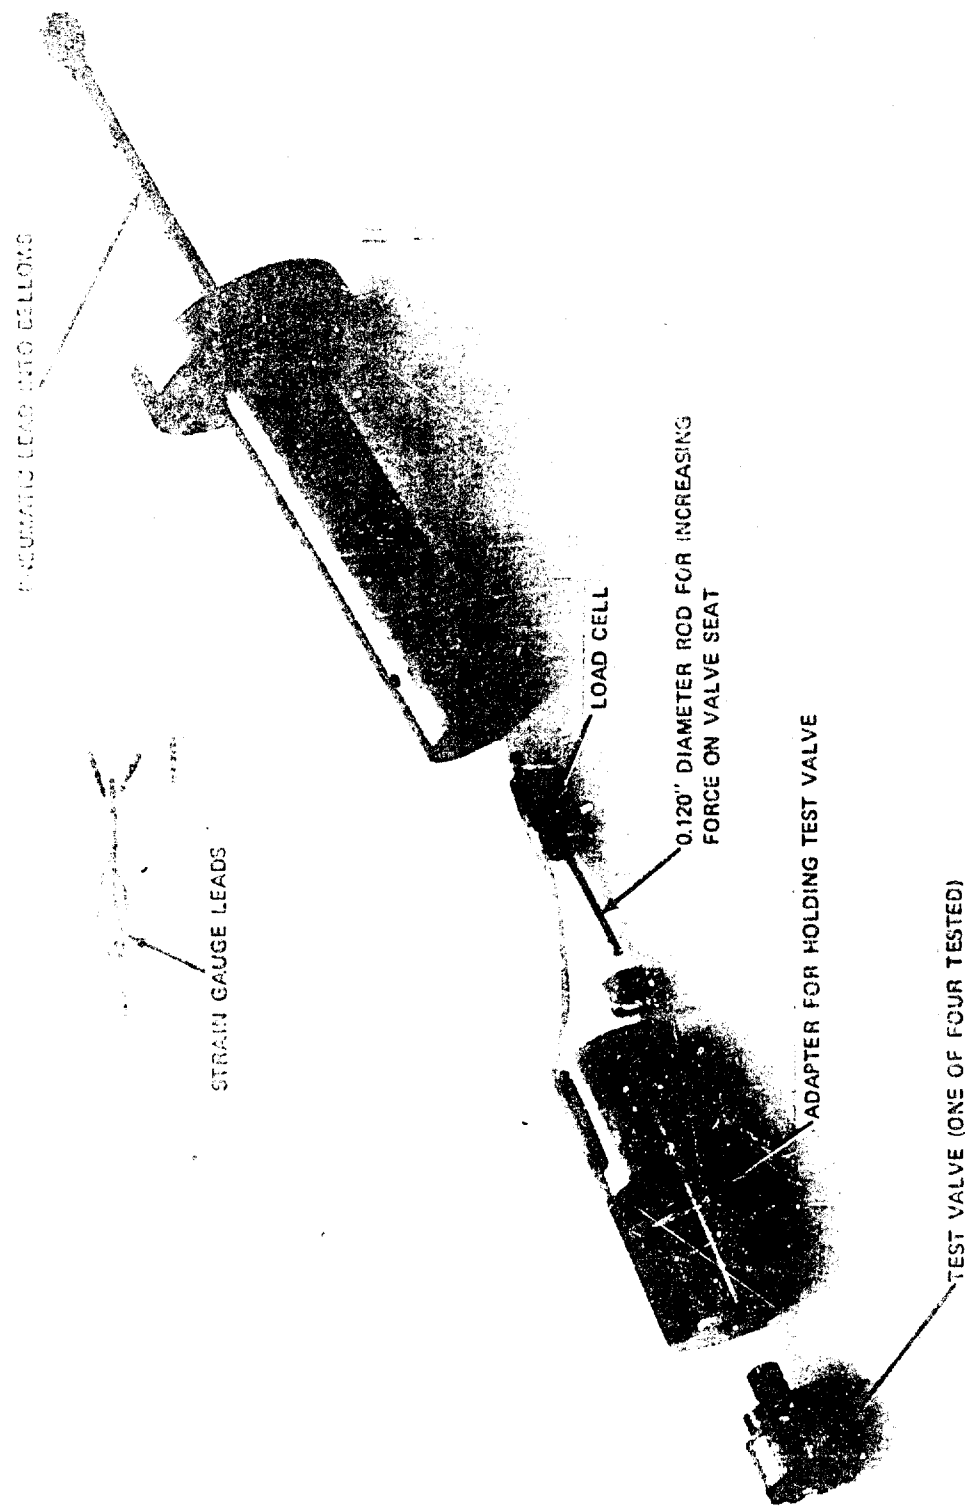oscilloscope trigger pulse was obtained from a 20X probe attached to the
Test Circuit. An electronic counter was also attached to the
Test Circuit (Computer Measurements Corporation Counter, Model No. 201B).
This counter gave a direct reading of the number of completed increased
stress cycles. A Chadwick and Helmuth pulse camera drive was used to
advance the 16 mm camera frame by frame. The input pulse for the camera
drive was obtained from a 8 volt DC relay connected to the Test
Circuit. Kodak Ektachrome type 7256 16mm film was used to obtain high
resolution photographs of the oscilloscope trace. Variations as small as
0.5 millisecond in a valve's opening time could be resolved on the
Ektachrome film.

IV.5   MICROSCOPE AND INTERFEROMETER

A CEJ Multimi No. 3000D Multiple Interference Microscope was used to
obtain height contours of the poppet and seat surfaces of each failed
valve. As its name implies, an interferometric method was incorporated
into the design of this instrument. Half of the wavelength of the light
used, conveniently called the interference step, constitutes the scale by
which the differences in height of the surface are measured. Thus the
scale is not affected by instrument errors. For example, the interference
step when using the green line of mercury is 10.75 microinches. The
surface contours were photographed with Polaroid film.

After each of the solenoid valves failed due to the application of
increased seating stresses, its seat and poppet were carefully examined
using a Bausch and Lomb StereoZoom microscope. This microscope magnifies
up to 60X, and has a special Polaroid camera attachment.

28

SECTION V

PROCEDURE

Each of the four solenoid valves was subjected to increasingly severe poppet-seat stresses. The increased seating stresses were effected by applying force to the rear of the poppet. This force was applied to the poppet by means of the 0.120" diameter steel rod. The force applied by the rod was regul⁻ by a pneumatic system outside the vacuum system. Motion was transr ¿d into the vacuum system through a one-half inch diameter steel b\ /ws.

Immediately prior to the tests described in this report, the four solenoid valves were refurbished by the Parker-Hannifin Corporation. This refurbishment included relapping the poppet-seat interface, adjustment of the sealing stress at the poppet-seat interface, and enlarging the valves' rear inlets. This last procedure was necessary in order to apply the 0.120" diameter steel rod to the rear of the poppet.

V.1   INCREASED STRESS TESTS

The force applied to the rear of the poppet was determined from the pressure in the pneumatic system and from strain gauges attached to the force-applicator rod. Using the pumps described in Section IV.1, the vacuum system was pumped down to a pressure of less than 10^{-6} torr in less than one hour.

The increased stress tests consisted of carrying out the following steps (see Fig. 15):

1. The Parker valve was closed (normal condition) and the solenoid control valves connected the bellows to the mechanical vacuum pump. The bellows was then in its neutral position and the separation distance of the stress-applicator rod and the valve poppet was ~ 0.1".

2. The solenoid control valves connected the aneroid manostat to the bellows. Compressed gas then flowed from the gas cylinder through the aneroid manostat into the small volume around the bellows. The aneroid manostat could be used to regulate the absolute pressure in the volume around the bellows over the range 0.8 to 60 inches of Hg to a precision of $\pm$ 0.02 inches of Hg. A valve in the manostat restricted the flow of gas; as a result, stress was applied slowly and smoothly to the rear of the poppet, and in turn, to the poppet of the Parker valve.

29

3. During the first few stress application cycles the force
   applied to the poppet was determined by monitoring strain
   gauges attached to the stress-applicator rod. At the
   conclusion of approximately 100 cycles, the force applied
   to the poppet was again measured by using the strain gauges.

4. After a few seconds of increased stress application, the
   solenoid control valves again connected the bellows to the
   mechanical vacuum pump; this removed the increased stress.

5. The Parker valve's solenoid was energized, and the solenoid's
   current waveform was monitored by an oscilloscope. The
   oscilloscope's trace was photographed by a sequence camera.
   If sticking was detected, the force required to separate the
   poppet from the seat was later determined from the solenoid
   current's waveform. The force required to open a sticking
   Parker valve was determined by comparing an abnormal delay
   in the valve's opening time (obtained from the solenoid
   current's waveform) with results of previous calibration
   tests performed in air (see Subsection V.2).

6. The Parker valve's solenoid was de-energized and the Parker
   valve closed.

7. The cycle started over again.

After being actuated for 1000 times at a given stress level, the valve
was removed from the vacuum chamber, its leak rate was measured, and if
its leak rate was satisfactory, it was subjected to further increased
stress tests (up to 40,000 psi). If the valve's leakage rate was unsatis-
factory, i.e., if the valve was judged to have failed, the failed valve's
poppet and seat were subjected to microscopic examination.

V.2   VALVE CALIBRATION

In order to relate the deviations of the opening time to any possible
sticking force at the poppet-seat interface, it was necessary to cali-
brate each value prior to the increased stress tests performed in
vacuum. This was done by observing the increase in the opening time
under ambient laboratory conditions as a function of additional stress
applied to the rear of the poppet by the 0.120" tungsten rod (See
Fig. 18). For example, an increase in the opening time of valve B520303
from its normal value of six seconds to ten seconds would imply the presence
of a sticking force of approximately one-half pound at the poppet-seat
interface. For the range of opening time deviations of interest, the
increase in the opening times were linear functions of the additional
applied stress. The stall condition of valve B520103 occurred at 3000 psi;
for the other three valves, the stall condition occurred at less than
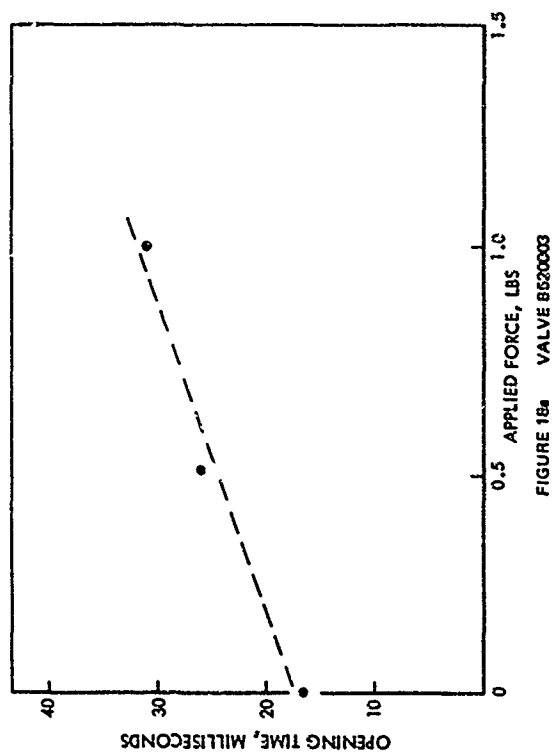1200 psi. The reason for this difference is explained in Section VI.
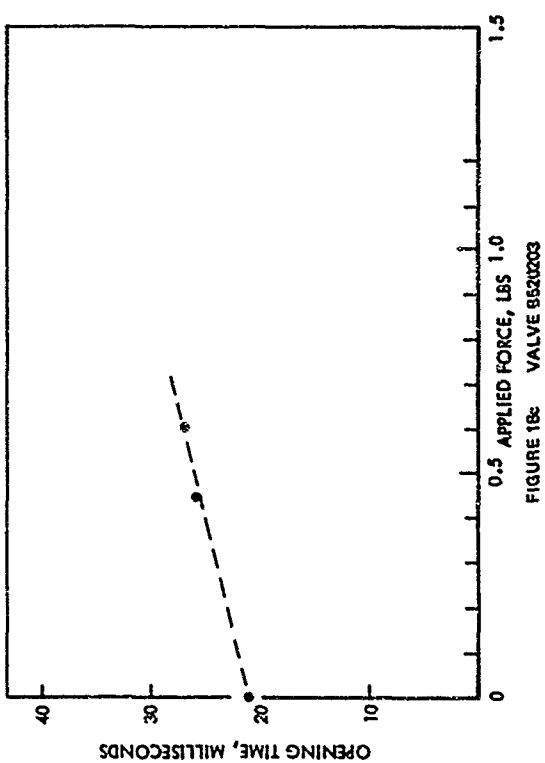
FIGURE 18b   VALVE B520103
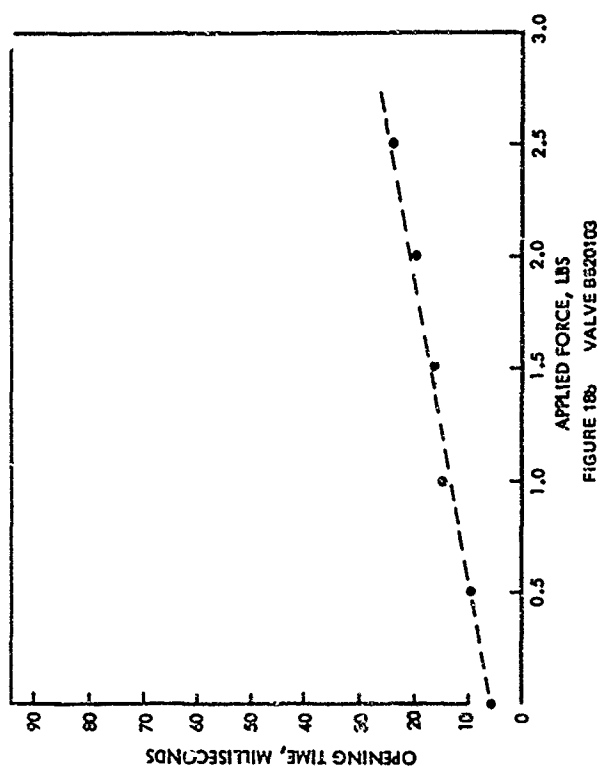
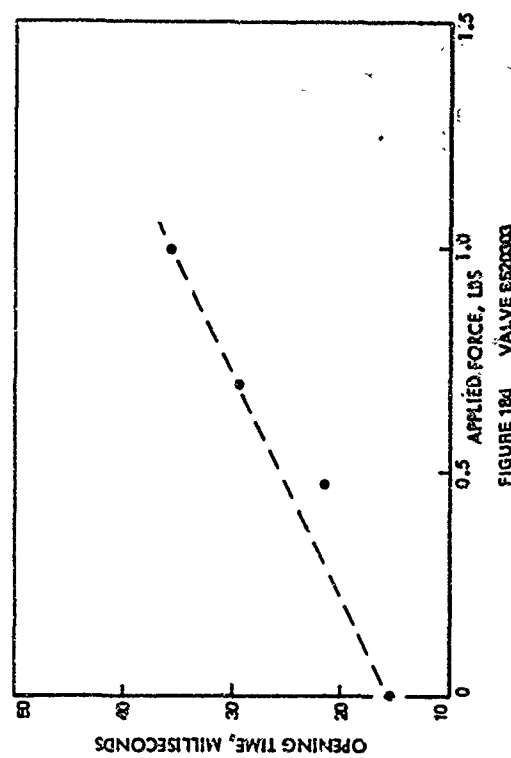FIGURE 18a   VALVE B520003

FIGURE 18d   VALVE B520203

FIGURE 18c   VALVE B520203

VALVE OPENING TIME AS A FUNCTION OF FORCED APPLIED TO THE REAR OF THE VALVE'S POPPET.

31

V.3   LEAKAGE TESTS

The leakage rate of each value was measured prior to each increased poppet-seat stress test. The leakage rates of the valves were measur d by using both nitrogen and helium gas to displace water from an inverted 100 ml graduate. Before the leakage tests were begun, all residual water was discharged from the terminal tip of the gas line, which was located directly under the inverted graduate. A 0.2 micron 1" O.D. Millipore filter was used to prevent contaminant particles from lodging on the seat or poppet surfaces and thus causing an erroneous measurement of leakage. The rate of volume displacement of the water was assumed to be equal to the leak rate of the solenoid valve. Three needle valves immediately upstream of the solenoid valve permitted the solenoid valve to be opened and closed several times between leakage measurements to dislodge any particles that may have been situated between the seat and poppet. The three needle valves also insured that water would not be accidentally drawn into the solenoid valve. The upstream pressure was read by a calibrated 0 to 60 psig Victor diaphram gauge.

V.4   MICROSCOPE AND INTERFEROMETER EXAMINATIONS

Two of the valves, No. 520003 (stainless steel and stainless steel) and B520103 (stainless steel and tungsten carbide), failed prior to completion of the increased seating stresses. These two valves were examined using the conventional microscope and the interference microscope. The remaining two valves which did not fail were not examined with these instruments.

SECTION VI

RESULTS AND DISCUSSION

VI.1   INCREASED SEATING STRESS TESTS

The results of the increased seating stress tests are shown in Tables
3 through 6. The helium and nitrogen leakage rates were measured outside
the vacuum system, i.e., under ambient laboratory conditions, before and
after each increased seating stress test. As discussed in Section V,
each increased seating stress test consisted of executing the following
cycle 1000 times:

1. The increased seating stress was applied for about six
    seconds and then removed.

2. The valve was opened for about 70 milliseconds and then
    closed (the increased seating stress was not applied
    during the actuation of the valve).

The average opening time for each valve, $\overline{t_2 - t_0}$, was calculated from the
expression

$$\overline{t_2 - t_0} = \sum_{i = 1}^{N} \frac{(t_2 - t_0)_i}{N}$$

where i denotes the actuation number and N denotes the total number of
actuations of the valve in question.

The value of $\overline{t_2 - t_0}$ for each of the valves was essentially independent of
the level of increased stress, and therefore the values given in Tables
3 through 6 represent values obtained by averaging over all the actuations
of a specific valve. Only valve B520103 exhibited relatively large devia-
tions in its opening time; the opening time deviations of the other three
valves had a normal distribution and were judged to be statistical
fluctuations.

The valves that failed, B520003 and B520103, exhibited different behavior
prior to failure. Valve B520003 did not stick at any time; valve B520103
experienced adhesion several times and even cold welded. The figures on
the following pages show solenoid current waveforms of valve B520103, these
photographs are enlargements of individual frames of the 16 mm Ektachrome
film and were taken during the 5600 psi test. These figures should be
compared with the normal current waveform of the same value shown in
Fig. 18. Fig. 19 shows an opening time of 15 ms; Fig. 20 shows an opening
time of 24 ms; and cold welding is indicated by Fig. 21. Table 7 gives the
opening times of valve B520103 (at an applied stress level of 5600 psi)
prior to when this valve cold welded.

33

TABLE 3

LEAKAGE AND STICKING DATA FOR VALVE B520003
(17-4PH STAINLESS STEEL AND 440C STAINLESS STEEL)

Applied Stress, psi x 10^3	0.35	0.70	1.4*	2.8	5.6	10	20	40
Helium Leakage Before (P_0 = 20 psig), cc per hour	2	7	4					
Helium Leakage After (P_0 = 20 psig), cc per hour	7	4	38					
Nitrogen Leakage Before (P_0 = 20 psig), cc per hour	2	4	6					
Nitrogen Leakage after (P_0 = 20 psig), per hour	4	6	20					
Mean Opening Time, Milliseconds	21.5 (Average for All Stress Levels)							
RMS Deviation from Mean Opening Time, Milliseconds	4.0 (Average for All Stress Levels)							
Sticking Force Corresponding to RMS deviation of Opening Time, lbs	0.264 (Average for All Stress Levels)							
Maximum Opening Time Deviation from Mean Opening Time, Milliseconds	5.0 (Maximum for All Stress Levels)							
Sticking Force Corresponding To Maximum Opening Time Deviation, lbs.	0.320 (Maximum for All Stress Levels)							

*Testing was terminated after the 1400 psi test.

TABLE 4

LEAKAGE AND STICKING DATA FOR VALVE B520103
(17-4PH STAINLESS STEEL AND TUNGSTEN CARBIDE)

Applied Stress, psi x 10^3	0.35	0.70	1.4	2.8	5.6*	10	20	40
Helium Leakage Before (p_o = 20 psig), cc per hour	13	16	14	10	12			
Helium Leakage After (p = 20 psig), cc per hour	16	14	10	12	588			
Nitrogen Leakage Before (p_o = 20 psig), cc per hour	9	8	12	9	10			
Nitrogen Leakage After (p_o = 20 psig), cc per hour	8	12	9	10	504			
Mean Opening Time, Milliseconds	6.5 (Average for All Stress Levels)							
RMS Deviation from Mean Opening Time, Milliseconds	0.2 (Average for All Stress Levels)							
Sticking Force Corresponding to RMS deviation of Opening Time, lbs.	0.02/ (Average for All Stress Levels)							
Maximum Opening Time Deviation from Mean Opening Time, Milliseconds	0.5	1.0	0.1	24.5	25.5			
Sticking Force Corresponding to Maximum Opening Time Deviation, lbs.	0.068	.136	.014	3.33	3.47			

*Testing was terminated after the 5600 psi test.

TABLE 5

LEAKAGE AND STICKING DATA FOR VALVE B520203
(440C STAINLESS STELL AND TUNGSTEN CARBIDE)

Applied Stress, psi x 10^3	0.35	0.70	1.4	2.8	5.6	10	20	40
Helium Leakage Before (p_0 = 20 psig), cc per hour	2	2	0	2	3	1	1	2
Helium Leadage After (p_0 = 20 psig), cc per hour	2	0	2	3	1	1	2	1
Nitrogen Leakage Before (p_0 = 20 psig), cc per hour	<1	2	<1	5	2	2	<1	4
Nitrogen Leakage After (p_0 = 20 psig), cc per hour	2	<1	5	2	2	<1	4	1
Mean Opening Times Milliseconds	21.5 (Average for All Stress Levels)							
RMS Deviation from Mean Opening Time, Milliseconds	0.5 (Average for All Stress Levels)							
Sticking Force Corresponding to RMS deviation of Opening Time, lbs.	0.05 (Average for All Stress Levels)							
Maximum Opening Time Deviation from Mean Opening Time, Milliseconds	5.5 (Maximum for All Stress Levels)							
Sticking Force Corresponding To Maximum Opening Time Deviation, lbs.	0.55 (Maximum for All Stress Levels)							

TABLE 6

LEAKAGE AND STICKING DATA FOR VALVE B520303
(TUNGSTEN CARBIDE AND TUNGSTEN CARBIDE)

Applied Stress, psi x 10^3	0.35	0.70	1.4	2.8	5.6	10	20	40
Helium Leakage Before ($P_0 = 20$ psig), cc per hour	6	3	5	3	4	4	4	3½
Helium Leakage After ($P_0 = 20$ psig), cc per hour	3	5	3	4	4	4	3½	4
Nitrogen Leakage Before ($P_0 = 20$ psig), cc per hour	3	4	4	3	3	2	2	1
Nitrogen Leakage After ($P_0 = 20$ psig), cc per hour	4	4	3	3	2	2	1	3
Mean Opening Time, Milliseconds	17.5*							8.5
RMS Deviation from Mean Opening Time, Milliseconds	0.5*							0.02
Sticking Force Corresponding to RMS deviation of Opening Time, lbs.	0.025*							1.0 x10^{-3}
Maximum Opening Time Deviation from Mean Opening Time, Milliseconds	3.5*							0
Sticking Force Corresponding to Macimum Opening Time Deviation, lbs.	0.175*							0

*These values are average values and apply at all levels of applied stress except 40,000 psi.
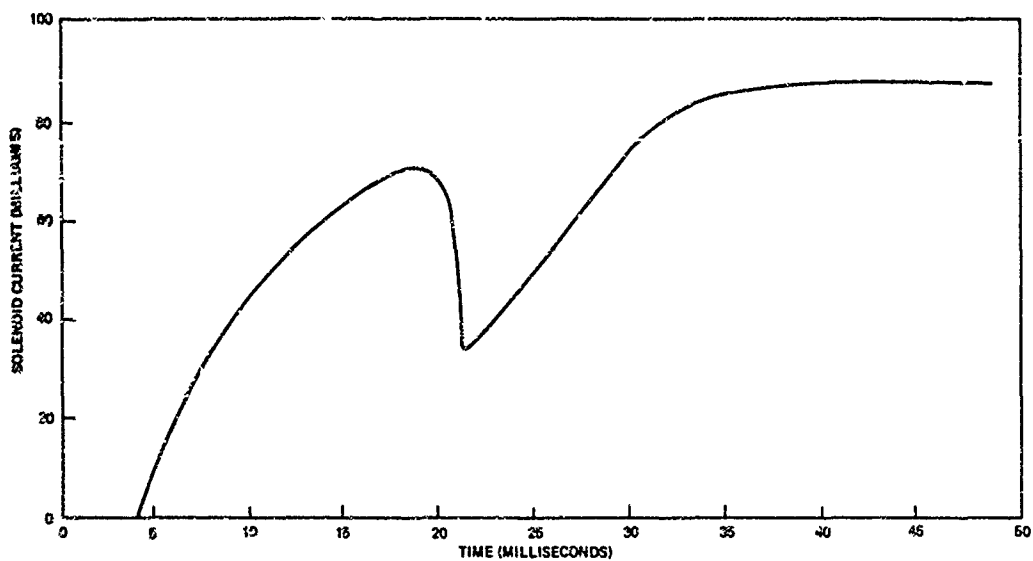
FIGURE 19   STICKING OF VALVE B520103

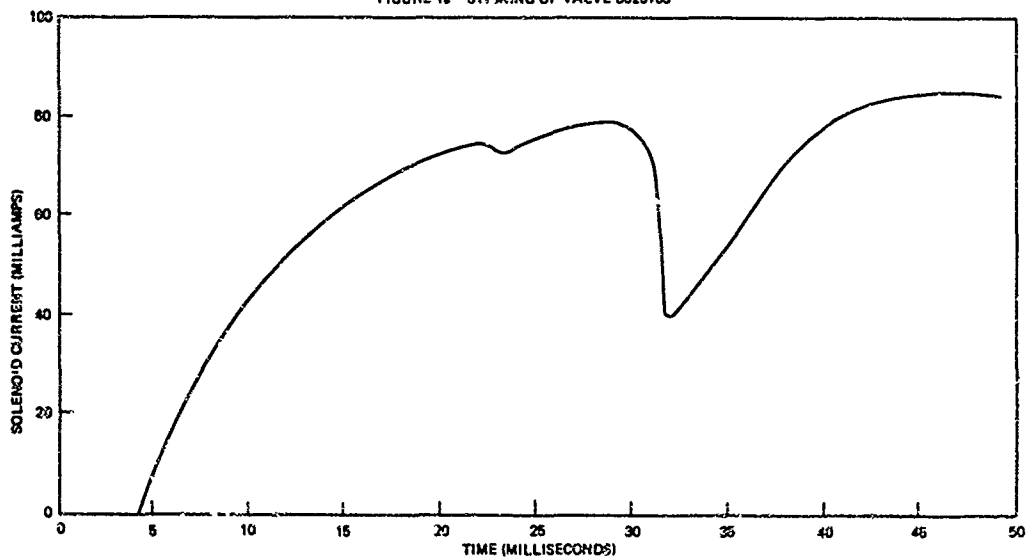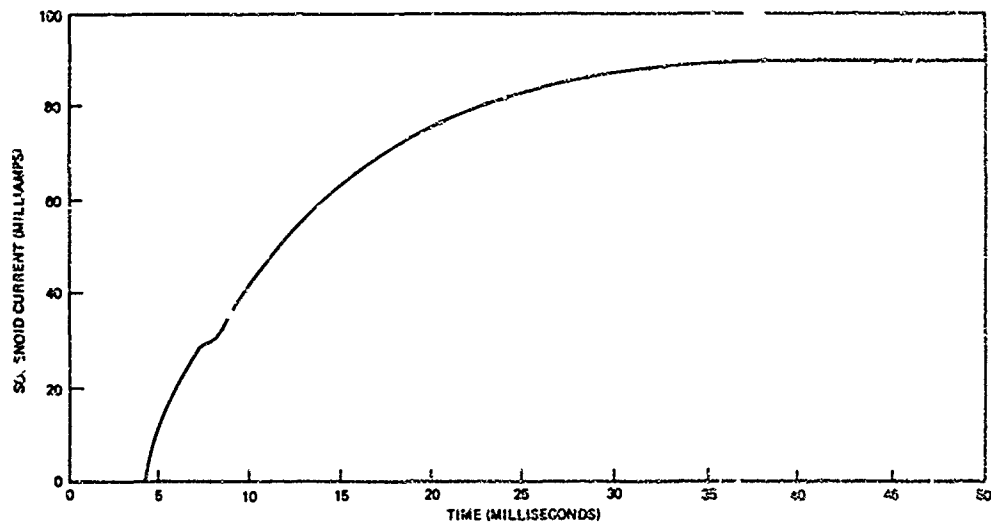FIGURE 20   STICKING OF VALVE B520103

FIGURE 21   COLD WELDING OF VALVE B510103

TABLE 7

OPENING TIME AS A FUNCTION OF
ACTUATION NUMBER
VALVE B520103
APPLIED STRESS = 5600 psi

The opening time of actuations not listed in the Table was 6 milliseconds.

Actuation Number	Opening Time (Milliseconds)
2	5
3	5
4	5
5	15
6	16
7	17
8	18
9	19
10	21
11	23
12	22
13	26
14	26
15	27
16	29
17	32
18	28
19	31
20	30
21	29
22	29
24	35
31	5
32	5
43	Cold Welded

Note that the mean opening time of valve B520103 was substantially shorter than the mean opening times of the other three valves. This resulted from the fact that it was necessary to increase the closing force exerted by the other three valves' belleville springs (see Fig. 2) in order to obtain acceptably low leak rates (less than about 10 cc per hour using 20 psig Helium). Increasing the closing force led to longer opening times for these three valves.*

Increasing the closing forces of the belleville springs put increased loads on the circuitry of the electronics package; as a result some of the transistors became too hot, and the electronics package gener- ated an output voltage which, rather than being square, exhibited substantial decay during the interval of its application across a valve's solenoid coil. An external circuit was attached to the electronics package to obtain a square voltage wave (about 9 volts) across the solenoids of valves B520003 and B520203. The external circuit was also attached to the test circuit during the 40,000 psi test of valve B520303; this explains the reduced opening time of that valve during the 40,000 psi test. It was thought that employing the external circuit during the 40,000 psi test would reduce the RMS deviation from the mean opening time, this conclusion proved to be correct.

VI.2   MICROSCOPE AND INTERFEROMETER EXAMINATIONS

Figs. 22a and 22b show the seat and poppet respectively (both stainless steel) of Valve B520003 at a magnification of about 2X. Note the extreme discolo- ration of the poppet in the sealing area. Fig. 23 shows the seat of valve B520003 at a magnification of about 50X. This photograph was obtained using the interference microscope. The light source was a hydrogen lamp and a green filter was used. The difference in height between adjacent fringes is one-quarter wavelength (about 12 Angstroms).

Figs. 24a and 24b show the seat (stainless steel) and poppet (tungsten car- bide) of valve B520103 at a magnification of about 30X. Note the damaged portion of the seat in Fig. 24a. The large number of scratches visable on the surface of the poppet (Fig. 24b) are due to the lapping process. Again note the extreme discoloration of the poppet in the sealing area.

FIGURE 22a

SEAT OF VALVE B520003
AFTER FAILURE (2X)

FIGURE 22b

POPPET OF VALVE B520003
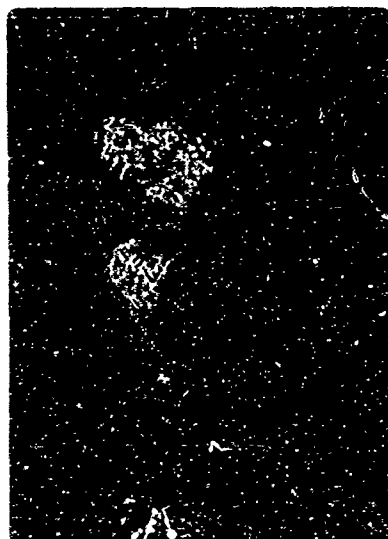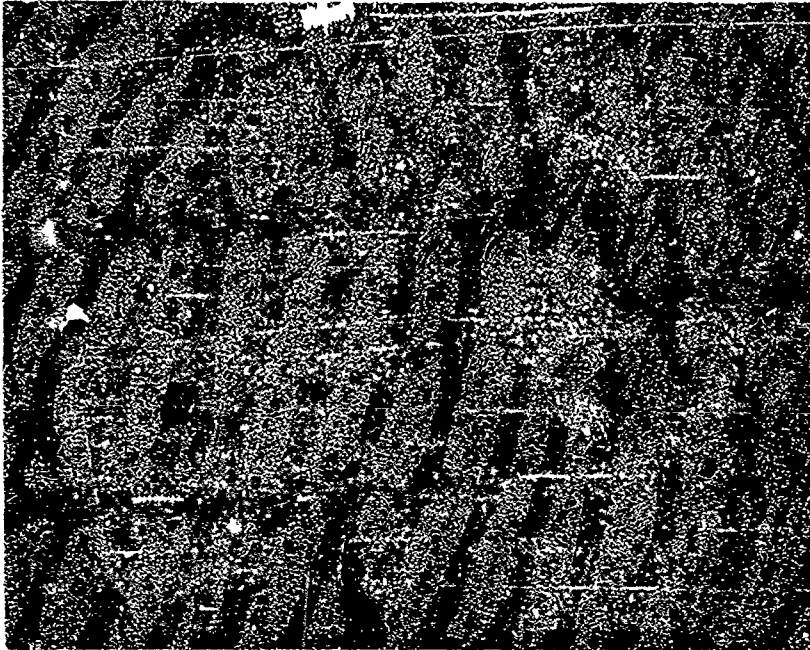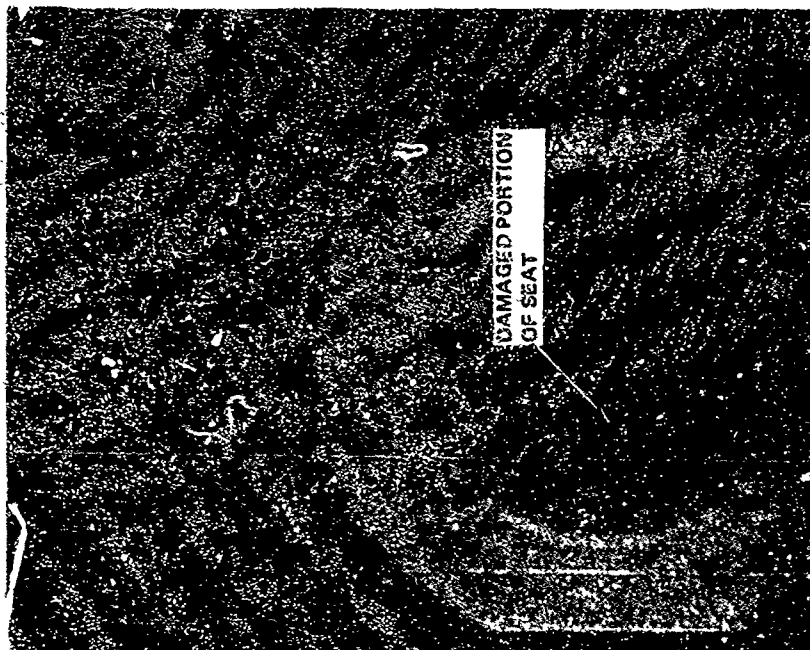AFTER FAILURE (2X)

FIGURE 23

SEAT OF VALVE B520003
AFTER FAILURE (50X)

FIGURE 24b   POPPET OF VALVE 6520103
               AFTER FAILURE

FIGURE 24a   SEAT OF VALVE 6520103
               AFTER FAILURE (30X)

DAMAGED PORTION
OF SEAT

42

VI.3   DISCUSSION

The results of both Phases I and II suggest that for the materials tested
the problem of cold welding between engineering surfaces experiencing
normal stress does not manifest itself until the stress approaches the
yield stress of one of the contacting surfaces. During Phase I, it was
observed that adhesion occurred only when the normal stresses were sub-
tantially higher than the yield stress of one of the surfaces. Valve
B520003 developed a high leakage rate, presumably due to seal deformation,
before any adhesion was detected. Valve B520103 experienced some adhesion
prior to developing a high leakage rate, but this valve developed a high
leakage rate immediately after the next increased stress test which was
performed at 5600 psi. However, the contact resistance data obtained
during Phase I substantiates th the environment inside the vacuum system
was at least as permissive as space. Recall from Section II that the
contact resistance data obtained using the supplemental contactor matched
the data obtained in space; and further, instances of cold welding and
adhesion were observed in the vacuum system and not in space.

In view of the fact that none of the solenoid valves experienced cold
welding in space, it is interesting to consider the probable margins
before failure existing in the valves during the tests in space. Direct
measurement of the static poppet seating force using an Instron Universal
Tensile Test Machine yielded the result that this force never exceeded
45 ± 20 grams for all valves. Note that the poppet seating force is not
the force required to move the armature but rather the force required to
compress the small spiral spring which presses the poppet against the
seat. The impact poppet seating force may be substantially higher than
the static poppet seating force. However, the force of 45 ± 20 grams is
substantially smaller than 0.70 lbs., the increased force level at which
all of the valves continued to function satisfactorily. Valves B520203
and B520303 can be considered to have had the highest margin of safety
since they dod not fail even at an increased stress level of 40,000 psi.

One difficulty related to the design of the four solenoid valves is
illustrated by Fig. 20. An irregularity in the valve's solenoid current
trace occurred at t = 23 milliseconds; and was probably produced by the
poppet's restraining clamp adhering to the valve's poppet. This adhesion
increased the opening time to approximately 27 milliseconds. The effect
of this adhesion is also evident in Fig. 21 at t = 7 milliseconds. Visual
inspection showed extreme wear at the regions of impact of the poppet's
restraining clamp and the valve's seat (see Fig. 2). It was observed
that no poppet wear occurred at the interface of the restraining clamp
and the poppet itself; therefore, no transmission of increased stress to
the poppet's restraining clamp occurred during the increased stress tests.
The observed wear was very extensive, and may even have led to the failure

43

of valves B520003 and B520103; wear particles which appeared to have come from the impact area of the restraining clamp and the seat were extensively distributed and even reached the valve's sealing surfaces. Future valve designs should avoid this type of secondary contact and wear.

Although the present work was limited to the study of one valve configuration incorporating only stainless steel and tungsten carbide, the results can be generalized to other applications: for example, other types of valves which experience only normal stresses, gimbal stops, and relays.

SECTION VII

SPACE FLIGHT QUALIFICATION TEST

VII.1   SCOPE

This recommended flight qualification test describes a procedure for
determining whether or not metallic surfaces will adhere in space as a
result of being subjected to exclusively normal stress. Relief valves,
main propellant valves, switches, and doors are examples of devices
employing metallic surfaces which experience normal stress. It is assumed
that the metallic surfaces have not been subjected to special cleaning
procedures designed to remove the chemically adsorbed oxide layer; it is
also assumed that the more easily removed contaminants such as dust,
grease, and other foreign matter have been removed from the surfaces.
Trichloroethylene or alcohol is appropriate for this purpose. It is
assumed that the contacting surfaces are not deformed during typical
operation of the device being tested, and that instrumentation is avail-
able which permits the opening time or force of the device to be measured.

VII.2   THE VACUUM SYSTEM

Except as noted below, the vacuum system construction techniques described
in ASTM E 332, "Recommended Practice for Combined, Simulated Space-
Environment Testing of Thermal Control Materials" shall be followed;
however, it is not necessary to cool the vacuum system's walls with
liquid nitrogen during a test.

The vacuum system shall contain no mercury or oil diffusion pumps. No
vacuum grease shall be used; copper seals are preferred, but the use of
Viton seals is permissible provided the seals are kept completely dry.
Ion or titanium sublimation pumps shall be used to maintain the total
pressure in the vacuum system below 10^{-8} torr as measured by a calibrated
ion gauge (see ASTM E 296 and E297, "Recommended Practice for Ionization
Gauge Application to Space Simulators" and "Methods for Calibrating
Ionization Vacuum Gauge Tubes", respectively). Cryogenic molecular sieve
roughing pumps shall be used; the use of a compressed air aspirator is
permissible. Mechanical pumps shall not be used as roughing pumps.

Electrical feedthroughs shall contain only metallized ceramic seals
(see ASTM F19, "Specifications for Metallized Ceramic Seals"). Electrical
leads inside the vacuum system shall either be bare or insulated with
specially treated fiberglass. The fiberglass shall be prepared by washing
it in alcohol and then heating it to 400°F to drive off the residual
alcohol.

The vacuum system components shall be cleaned by ultrasonic techniques,
and the components shall be dried in warm air ovens. Technicians working
on the vacuum system shall wear vinyl inspectors' gloves when handling
interior vacuum system components. Bench work shall be performed on
laminar flow benches. Mechanical feedthroughs shall have a minimum
number of moving parts, and no unnecessary equipment shall remain in the
vacuum system.

VII.3   PROCEDURE

Each space flight qualification test should be designed for the unique conditions peculiar to the situation involved. The detailed test procedure should be prepared after consultation and review with the equipment designer (or manufactuer) and the user. Special situations in the flight test plan should be reflected in a detailed test plan designed for the particular conditions expected. This test plan is designed for assurance that exposure to the vacuum of space will not degrade system operation. The recommended general procedure is as follows:

1. Close off the vacuum system and begin pumpdown.

2. Bake-out the vacuum system if necessary to reach a pressure of 10^{-8} torr. Do not exceed the thermal limitations of the device which will be tested.

3. Identify and correct any leaks or sources of excessive outgassing.

4. Subject the test article to a bench test. During this test the device should execute at least 10% of the cycles correspondong to the mission requirement. Abnormalities in the opening time should be absent.

5. Install the device in the vacuum system and backfill the vacuum system to a pressure of one atmosphere using dry nitrogen gas. Remove any covers or enclosures which would inhibit outgassing of the contacting surfaces. Purge chamber with gaseous nitrogen.

6. Prior to pumpdown retest the device. During this test the device should execute at least 10% of the cycles corresponding to its mission requirement. Abnormalities in the opening time or force should be absent.

7. Pump the vacuum system down to 10^{-5} torr. A mild bake-out is permissable if the thermal limitations of the device are not exceeded.

8. Elevate the temperature of the device to a level ten to twenty percent above the maximum temperature it will experience during the mission.

9. Subject the device to prolonged life cycle testing. During this test the device should execute at least 300% of the cycles corresponsing to the mission requirement. Any particularly severe operational program should be executed at least three times. Abnormalities in the opening time should be absent throughout these tests.

10. Vent the vacuum system to the atmosphere and remove the device from the vacuum system. Re-attach any covers or enclosures which were removed in Step 5.

11. Subject the device to a final bench test. During this test the device should execute at least 10% of the cycles corresponding to the mission requirement. Abnormalities in the opening time should be absent.

47

REFERENCES

1. "Rockets in Space Environment", Contract AF04(611)-7441, Aerojet-General Corporation, RPL-TDR-63-1050, Vol 1, AD416294, Vol 2 AD416157.

2. "ERS Valve Certification Tests" AFRPL In-House, AFRPL-TR-65-84, May 1965 AD464155.

3. "Study of Vacuum Welding" Contract AF94(1)-9717, National Research Corp, AFRPL-TR-66-105, AD815721, Jan 1967.

4. "In-Space Cold Welding Tests", Contract AF04(611)-9883, TRW Systems, AFRPL-TR-67-1, AD380181.

5. "A Study of Space Propulsion System Experiments Utilizing Environmental Research Satellites", Contract AF04(611)-9956, TRW Systems, Final Report May 1965, AFRPL-TR-65-73, AD464581.

6. "Environmental Research Satellites for Space Propulsion System Experiments", 3rd Quarterly Progress Report, Contract AF04(611)-10747, TRW Systems, AFRPL-TR-66-178, AD486835, Jan. - March 1966.

7. "Environmental Research Satellites for Space Propulsion Systems," 4th Quarterly Progress Report, Contract AF04(611)-10747, TRW Systems, AFRPL-TR-66-290, AD8016 +   1966.

8. "AFRPL Orbital/Ground Experiments in Surface Adhesion Mechanics" CPIA Technical Paper L68-49, 10th Liquid Propulsion Symposium, Las Vegas, Nevada 1968, Volume 1, pages 350-374, CPIA Publication No. 176, Oct. 1968

9. "Cold Welding Research Phase I Report" Contract F04611-68-C-0077, Philco-Ford Corp., AFRPL-TR-68-211, January 1969 AD 847134

DOCUMENT CONTROL DATA - R & D
(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)

1 ORIGINATING ACTIVITY (Corporate author)	2a. REPORT SECURITY CLASSIFICATION
Philco-Ford Corporation 3825 Fabian Way Palo Alto, Calif. 94303	Unclassified 2b. GROUP

3 REPORT TITLE

Cold Welding Research Final Report

4 DESCRIPTIVE NOTES (Type of report and inclusive dates)

Experimental Test Program May 1968 to September 1969

5 AUTHOR(S) (First name, middle initial, last name)

Duncan B. Sheldon

6 REPORT DATE	7a. TOTAL NO OF PAGES	7b. NO OF REFS
January 1970		Nine
8a. CONTRACT OR GRANT NO F04611-68-C-0077 b. PROJECT NO 3058 c. d.	9a. ORIGINATOR'S REPORT NUMBER(S) TR-DA2175 9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report) AFRPL-TR-69-209	

10 DISTRIBUTION STATEMENT   This document is subject to special export controls and each transmittal to foreign governments or foreign nationals may be made only with prior approval of AFRPL (RPPR/STINFO). Edwards, CA 93523

11 SUPPLEMENTARY NOTES	12. SPONSORING MILITARY ACTIVITY Air Force Rocket Propulsion Laboratory Edwards Air Force Base, California

13 ABSTRACT

During Phase I of this research, a small experimental contactor was used to obtain electrical contact resistance data in air and in vacuum. These data show that an electronically-pumped vacuum system can effectively simulate the vacuum of actual space: the contact resistance data obtained in vacuum was in agreement with contact resistance data obtained from two small earth satellites. During Phase II, four solenoid valves were tested in the same electronically-pumped vacuum system used during Phase I; the test results were compared with adhesion data generated by identical valves during space flight tests. The contacting surfaces of the valves and the experimental contactor experienced only normal stresses. In order to determine the margin before failure existing in each of   valves during the space flight tests, incrementally increasing stresses were applied to the valves' sealing surfaces. The results of Phases I and II show that cold welding in space occurs near or above the yield point of one of the surfaces. A space-flight qualification test was written.

DD FORM 1 NOV 65 1473

KEY WORDS	LINK A		LINK B		LINK C	
	ROLE	WT	ROLE	WT	ROLE	WT
Cold Welding						
Electrical Contact Resistance						
Vacuum Welding						
Space Environmental Effects						